GGB
BY TIMKEN

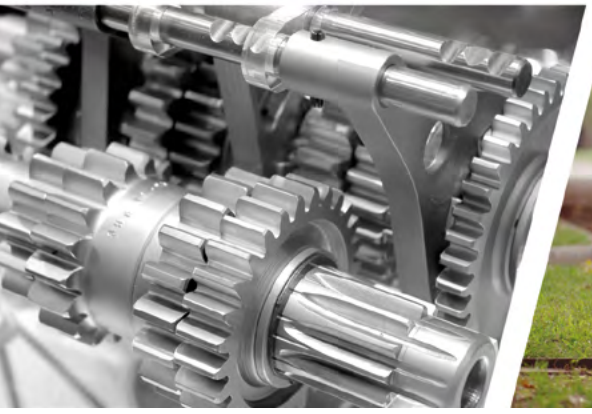

DP4® and DP4-B

METAL-POLYMER SELF-LUBRICATING LEAD-FREE BEARING SOLUTIONS

Who we are

GGB helps create a world of motion with minimal frictional loss through plain bearing and surface engineering technologies. With global R&D, testing, and production facilities, GGB partners with customers worldwide on customized tribological design solutions that are efficient and environmentally sustainable. GGB's engineers bring their expertise and passion for tribology to a wide range of industries, including automotive, aerospace and industrial manufacturing. To learn more about tribology for surface engineering from GGB, visit **ggbearings.com**.

Our products are used in tens of thousands of critical applications every day on our planet. It is always our goal to provide superior, high-quality solutions for our customers' needs, no matter where those demands take our products. From space vehicles to golf carts and virtually everything in between, we offer the industry's most extensive range of high performance, maintenance-free bearing solutions for a multitude of applications:

Aerospace

Agriculture

Automotive

Construction

E-Mobility

Energy

Exoskeletons

Fluid Power

Industrial

Medical

Mining

Oil & Gas

Primary Metals

Railway

Recreation

Robotics & Automation

The GGB Advantage

MAINTENANCE-FREE

GGB bearings are self-lubricating, making them ideal for applications requiring long bearing life without continuous lubrication.

LOW FRICTION, HIGH WEAR RESISTANCE

Low coefficients of friction eliminate the need for lubrication, while providing smooth operation, reducing wear and extending service life.

NVH (NOISE, VIBRATION, HARSHNESS)

Plain bearings provide a smooth sliding motion between surfaces and their material properties and simple design reduce noise, vibration and harshness.

LOWER SYSTEM COST

A one-piece design offers space and weight reductions and thanks to the material compositions and self-lubricating properties, less maintenance is needed.

REDUCED CO_2 FOOTPRINT

GGB's flexible and local production platforms assure timely deliveries and reduced CO_2 footprint.

PARTNER SUPPORT

GGB offers tribological, application and design support, and partners with our customers to provide the most efficient solutions.

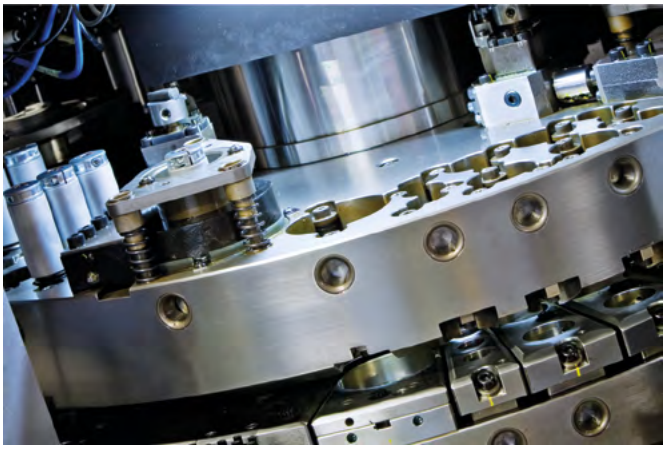

The Highest Standards in Fabrication

Our world-class manufacturing plants in the United States, Brazil, China, Germany, France and Slovakia are certified in quality and excellence according to ISO 9001, IATF 16949, ISO 14001 and ISO 45001. This allows us to access the industry's best practices while aligning our management system with global standards.

For a complete listing of our certifications, please visit our website:

ggbearings.com/en/certificates

What is Tribology

TRIBOLOGY IS THE SCIENCE OF FRICTION, WEAR, AND LUBRICATION

Tribology is the science of wear, friction and lubrication, and encompasses how interacting surfaces and other tribo-elements behave in relative motion in natural and artificial systems. This includes bearing design and lubrication.

TRIBOLOGY SURROUNDS YOU

Tribology is everywhere where contacting surfaces are in relative movement to each other.

THE TRIBOLOGICAL SYSTEM

Tribology is a complex science, involving 2 surfaces in relative motion that are subject to constant mechanical, thermal and chemical interaction.

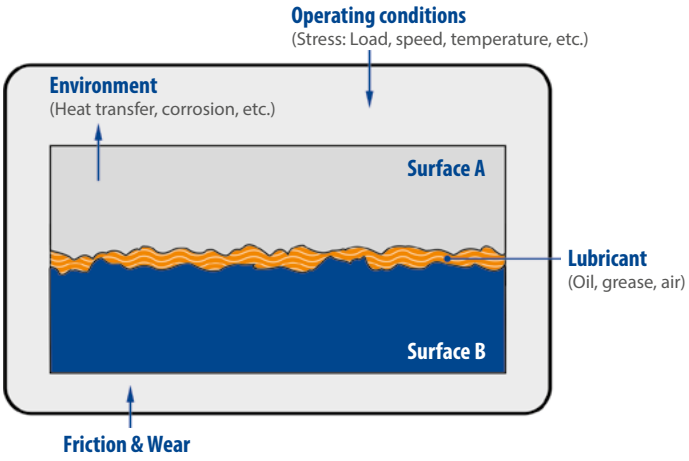

Table of Contents

1 Introduction 7

1.1 Characteristics and Advantages 7

1.2 Applications 8

2 Structure and Composition 9

2.1 Basic Forms 9
Standard Components 9
Non-Standard Components 9

3 Properties 10

3.1 Physical and Mechanical Properties 10

3.2 Chemical Resistance 10

3.3 Frictional Properties 11
Effect of Temperature for Unlubricated Applications 11

4 Bearing Performance 12

4.1 McPherson Strut Applications 12
Wear and Friction Properties 12
McPherson Strut Test Rig 12
Cavitation Erosion Resistance 14
Flow Erosion Resistance 15

4.2 Hydraulic Applications 16
GGB Jupiter Test Rig 16

4.3 Dry Wear Performance 17
Design Factors 17
Specific Load P 17
Sliding Speed V 18
Continuous Rotation 18
Oscillating Movement 18
PV Factor 19
Application Factors 19
Temperature 19
Mating Surface 20
Bearing Size 20
Bore Burnishing 21
Type of Load 21

4.4 Calculation of Bearing Service Life 22
Specific Load P 22
High Load Factor aE 22
Modified PV Factor 22
Estimation of Bearing Life LH 23
Bore Burnishing 23
Slideways 23

4.5 Worked Examples 24

5 Lubrication 25

5.1 Lubricants 25

5.2 Tribology 25
Hydrodynamic Lubrication 25
Mixed Film Lubrication 26
Boundary Lubrication 26

5.3 Characteristics of Lubricated Bearings 27

5.4 Design Guidance 28

5.5 Clearances for Lubricated Operation 29

5.6 Grooving for Lubricated Operation 29

5.7 Mating Surface Finish for Lubricated Operation 29

5.8 Grease Lubrication 29

6 Bearing Assembly 30
Dimensions and Tolerances 30

6.1 Allowance for Thermal Expansion 30

6.2 Tolerances for Minimum Clearance 30
Burnishing 31

6.3 Counterface Design 31

6.4 Installation 32
Fitting of Cylindrical Bushes 32
Fitting of Flanged Bushes 32
Insertion Forces 32
Alignment 33
Sealing 33

6.5 Axial Location 33
Fitting of Thrust Washers 33
Slideways 34

7 Modification 35

7.1 Cutting and Machining 35
Drilling Oil Holes 35
Cutting Strip Material 35

7.2 Electroplating 35
DP4® Components 35

Table of Contents

8	**Standard Products**	**36**
8.1	**DP4® Cylindrical Bushes - metric sizes**	**36**
8.2	**DP4® Cylindrical Bushes - inch sizes**	**42**
8.3	**DP4® Flanged Bushes - metric sizes**	**44**
8.4	**DP4® Flanged Bushes - inch sizes**	**46**
8.5	**DP4® Thrust Washers - metric sizes**	**47**
8.6	**DP4® Thrust Washers - inch sizes**	**48**
8.7	**DP4® Flanged Washers - metric sizes**	**49**
8.8	**DP4® Plates - metric sizes**	**50**
8.9	**DP4-B Cylindrical Bushes - metric sizes**	**51**
8.10	**DP4-B Flanged Bushes - metric sizes**	**54**
8.11	**DP4-B Plates - metric sizes**	**55**
9	**Test Methods**	**56**
9.1	**Measurement of Wrapped Bushes**	**56**
	Test A of ISO 3547 Part 2	56
	Test B (alternatively to Test A)	56
	Test C	56
	Measurement of Wall Thickness (alternatively to Test C)	56
	Test D	56
10	**Data Sheet for Bearing Design**	**57**
	Formula Symbols and Designations	58
	Product Information	59

1 Introduction

The purpose of this handbook is to provide comprehensive technical information on the characteristics of DP4® and DP4-B bearings.

The information given permits designers to establish the correct size of bearing required and the expected life and performance.

In addition, your local sales representative is available to assist you with your design. Complete information on the range of DP4® standard stock products is given together with details of other DP4® products.

GGB is continually refining and extending its experimental and theoretical knowledge and, therefore, when using this brochure it is always worthwhile to contact GGB should additional information be required.

As it is impossible to cover all conditions of operation which arise in practice, customers are advised to carry out prototype testing wherever possible.

1.1 CHARACTERISTICS AND ADVANTAGES

The DP4® and DP4-B materials offer the following characteristics:

- Good frictional properties with negligible stick-slip
- High static and dynamic load capacity
- Suitable for rotating, oscillating, reciprocating and sliding movements
- Compact size and low weight
- Prefinished material that requires no machining
- Possibility to burnish for reduced operating clearance
- No water absorption and therefore dimensionally stable
- Suitable for a wide operating temperature range from - 200 to +280 °C
- DP4-B with bronze backing for increased corrosion resistance
- Lead free in compliance with European RoHS 2002/95/EC, 2002/96/EC and EVL 2000/53/EC directives (see page 59)

In particular, depending on the dry running conditions, DP4® and DP4-B materials present the following performance advantages:

DRY CONDITIONS

- Good friction and wear performance under light duty conditions
- Particularly suitable for intermittent oscillating and reciprocating movements
- Maintenance-free as no external lubrication required
- Seizure resistant.

LUBRICATED CONDITIONS

- Good wear and friction performance over a wide range of load, speed and temperature conditions
- High wear resistance in boundary operating conditions
- High resistance of bearing surface under fluid cavitation and flow erosion conditions
- Suitable for operation in diverse fluids (oil, fuel, solvents, refrigerants, water).

1 Introduction

1.2 APPLICATIONS

Given the performance characteristics in both dry and lubricated operating conditions, DP4® and DP4-B bearing materials are extensively used in a wide range of automotive and industrial applications, such as:

AUTOMOTIVE

Braking systems, clutches, gearbox and transmissions, hinges - door bonnet and boot, convertible roof tops, pedal systems, pumps - axial, radial, gear and vane, seat mechanisms, steering systems, struts and shock absorbers, wiper systems.

INDUSTRIAL

Aerospace, agricultural, construction equipment, food and beverage, marine, material handling, office equipment, packaging equipment, pneumatic and hydraulic cylinders, railroad and tramways, textile machinery, valves.

2 Structure and Composition

DP4® / DP4-B

DP4® is a composite bearing material. It consists of a steel DP4® / bronze DP4-B backing to which is bonded a porous sinter bronze interlayer which is overlaid and impregnated with Polytetrafluoroethylene (PTFE) containing a mixture of inorganic fillers and special polymer fibres. The steel DP4® / bronze DP4-B backing provides mechanical strength and the bronze sinter layer provides a strong mechanical bond for the filled bearing lining.

Fig.1: DP4 microsection

Fig.2: DP4-B microsection

2.1 BASIC FORMS

STANDARD COMPONENTS

These products are manufactured to International, National or GGB standards. The following components are standard stock products:

– Cylindrical Bushes – Flanged Bushes – Thrust Washers – Flanged Washers – Plates

Fig.3: Standard stock products

NON- STANDARD COMPONENTS

These products are manufactured to customer's requirements and include for example:

– Modified Standard Components – Half Bearings – Flat Components – Deep Drawn Parts – Pressings – Stampings

Fig.4: Non-standard components

3 Properties

3.1 PHYSICAL AND MECHANICAL PROPERTIES

BEARING PROPERTIES		SYMBOL	UNIT	VALUE DP4®	VALUE DP4-B	COMMENTS
PHYSICAL PROPERTIES						
Coefficient of linear thermal expansion	parallel to surface normal to service	α_1 α_2	10^{-6}/K	11 30	18 36	
Operating temperature		T_{max} T_{min}	°C	+280 - 200	+280 - 200	
MECHANICAL PROPERTIES						
Compressive yield strength		σ_C	MPa	350	300	measured on disc Ø 25 mm x 2.45 mm thick
Maximum load	static dynamic	$P_{sta.max}$ $P_{dyn.max}$	MPa	250 140	140 140	

Table 1: Physical and mechanical properties of DP4 and DP4-B

CHEMICAL	%	°C	DP4®	DP4-B
STRONG ACIDS				
Hydrochloric Acid	5	20	-	-
Nitric Acid	5	20	-	-
Sulfuric Acid	5	20	-	-
WEAK ACIDS				
Acetic Acid	5	20	-	o
Formic Acid	5	20	-	o
BASES				
Ammonia	10	20	o	-
Sodium Hydroxide	5	20	o	o

CHEMICAL	°C	DP4®	DP4-B
SOLVENTS			
Acetone	20	+	+
Carbon Tetrachloride	20	+	+
LUBRICANTS AND FUELS			
Paraffin	20	+	+
Gasoline	20	+	+
Kerosene	20	+	+
Diesel Fuel	20	+	+
Mineral Oil	70	+	+
HFA-ISO46 High Water Fluid	70	+	+
HFC-Water-Glycol	70	+	+
HFD-Phosphate Ester	70	+	+
Water	20	o	+
Sea Water	20	-	o

Table 2: Chemical Resistance of DP4 and DP4-B

\+ Satisfactory: Corrosion damage is unlikely to occur

o Acceptable: Some corrosion damage may occur but this will not be sufficient to impair either the structural integrity or the tribological performance of the material

\- Unsatisfactory: Corrosion damage will occur and is likely to affect either the structural integrity and/or the tribological performance of the material

ELECTROCHEMICAL CORROSION

DP4-B should not be used in conjunction with aluminium housings due to the risk of electrochemical corrosion in the presence of water or moisture.

3.3 FRICTIONAL PROPERTIES

DP4® bearings show negligible 'stick-slip' and provide smooth sliding between adjacent surfaces. The coefficient of friction of DP4® depends upon:

– The specific load P [MPa]
– The sliding speed V [m/s]
– The roughness of the mating running surface R_a [µm]
– The bearing temperature T [°C].

A typical relationship is shown in Fig. 5, which can be used as a guide to establish the actual friction under clean, dry conditions after running in. Exact values may vary by ±20 % depending on operating conditions. Before running in, the friction may be up to 50 % higher.

After progressively longer periods of dwell under load (e.g. hours or days) the static coefficient of friction on the first movement may be between 1.5 and 3 times greater, particularly before running in.

EFFECT OF TEMPERATURE FOR UNLUBRICATED APPLICATIONS

The coefficient of friction of DP4® varies with temperature. Typical values are shown in Fig. 6 for temperatures up to 250 °C. Friction increases at bearing temperatures below 0 °C. Where frictional characteristics are critical to a design they should be established by prototype testing.

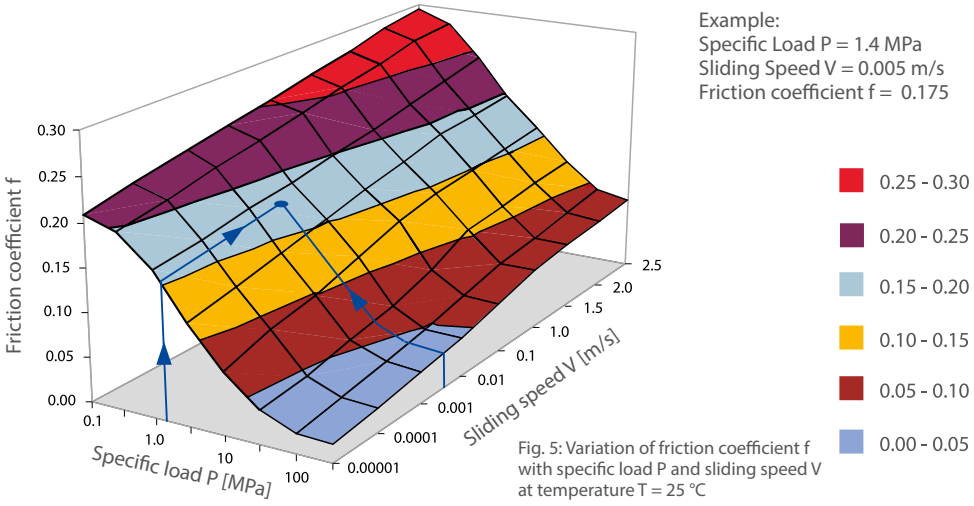

Fig. 5: Variation of friction coefficient f with specific load P and sliding speed V at temperature T = 25 °C

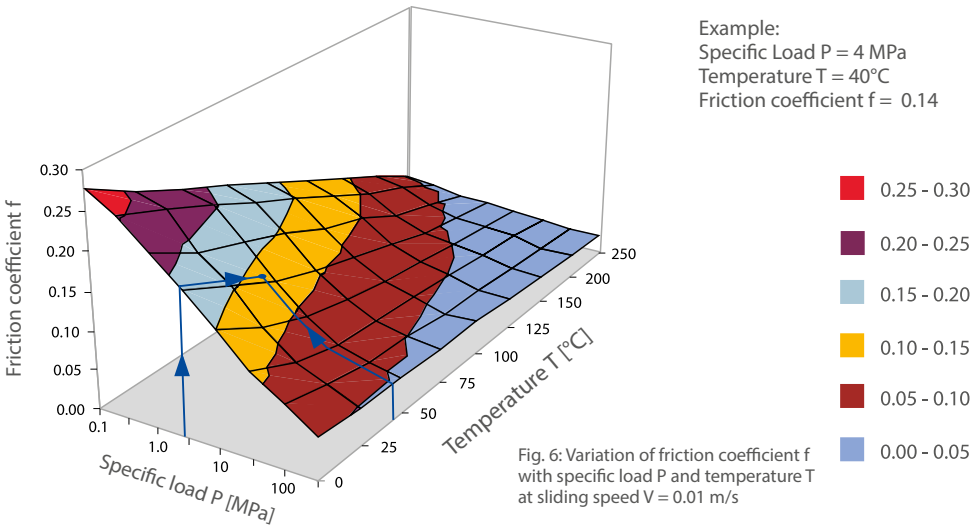

Fig. 6: Variation of friction coefficient f with specific load P and temperature T at sliding speed V = 0.01 m/s

4 Bearing Performance

4.1 MCPHERSON STRUT APPLICATIONS

DP4® has been developed to provide improved wear, erosion resistance and reduced friction in McPherson strut piston rod guide bush applications under the most demanding of operating conditions.

In the following sections, the performance of DP4® is compared with that of the material used in the majority of this type of application.

WEAR AND FRICTION PROPERTIES

The wear and frictional performance of DP4® has been evaluated in the piston rod guide bush application of a McPherson strut shock absorber using the test rig shown in Fig. 7. The test conditions are designed to simulate the operational duty of the test strut in service and differ in detail according to the strut manufacturer. The test conditions used are given in Table 3 and Table 4.

MCPHERSON STRUT TEST RIG

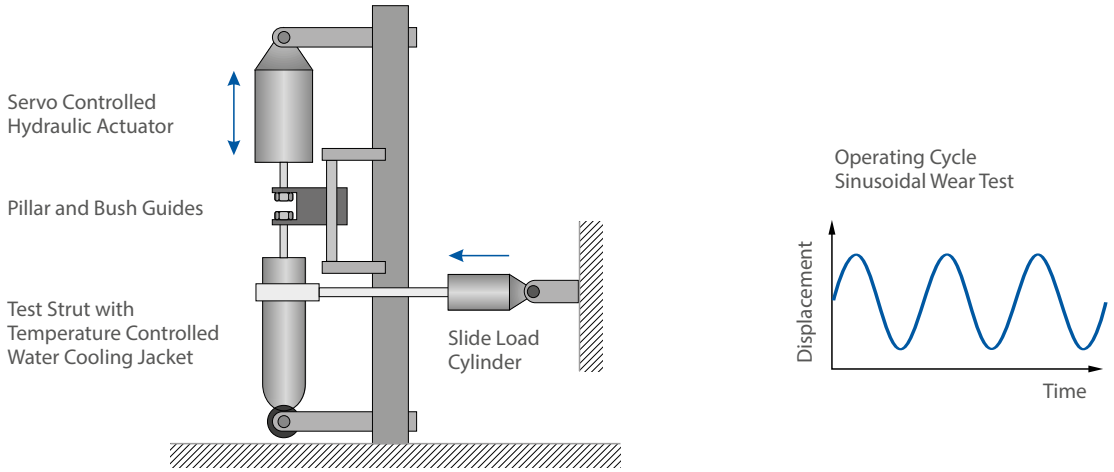

Fig. 7: Principle of the strut test rig

STRUT WEAR - TEST CONDITIONS	
Waveform	Sine
Frequency	2.5 Hz
Side load	890 N
Test duration	100 hours
Stroke	100 mm
Mean diametral clearance	0.06 mm
Lubricant	TEX 0358
Foot valve temperature	70 °C

Table 3: McPherson strut wear test conditions

STRUT FRICTION - TEST CONDITIONS	
Waveform	Sine
Frequency	0.1 Hz
Side load	600 N
Stroke	70 mm
Mean diametral clearance	0.06 mm
Lubricant	TEX 0358
Foot valve temperature	ambient

Table 4: McPherson strut friction test conditions

The relative wear and frictional performance of DP4® tested under these conditions are shown in Figures 8 - 10. Actual results for the wear rate and friction are not quoted because these depend strongly on the actual test conditions and design of the strut under test. The relative performance plots shown thus provide the best indication as to the benefits offered by DP4® in this class of application.

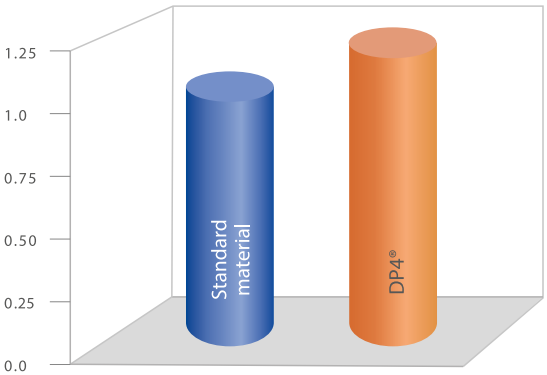

Fig. 8: Relative wear resistance

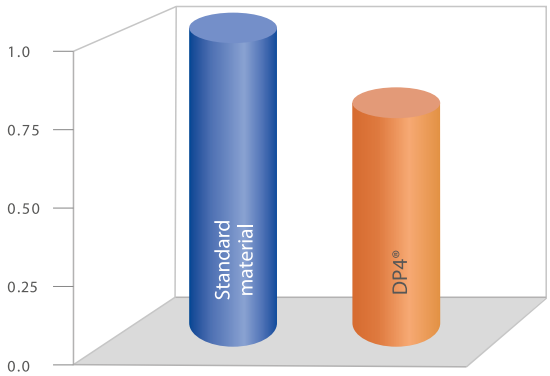

Fig. 9: Relative static friction coefficient

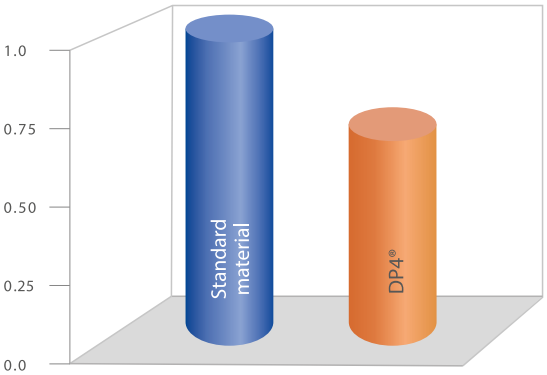

Fig. 10: Relative dynamic friction coefficient

4 Bearing Performance

CAVITATION EROSION RESISTANCE

Under certain operating conditions, the PTFE lining of the McPherson strut piston rod guide bush can suffer erosion damage, due to cavitation and flow erosion effects from the oil film within the bearing. The test rig shown in Fig. 11 is designed to reproduce the cavitation erosion damage to the bearing lining of the test specimen. The test conditions are given in Table 5.

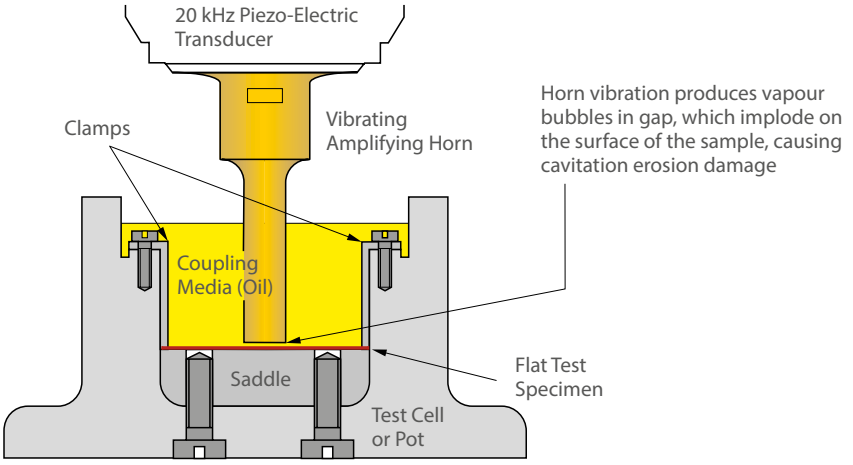

Fig. 11: Principle of the cavitation erosion test rig

CAVITATION EROSION - TEST CONDITIONS	
Amplitude	0.015 mm
Frequency	20 kHz
Separation	1 mm
Test duration	30 minutes
Lubricant	TEX 0358
Temperature	ambient

Table 5: Cavitation erosion test conditions

The relative resistance to cavitation damage of DP4® as evaluated on this test rig is shown in Fig. 12.

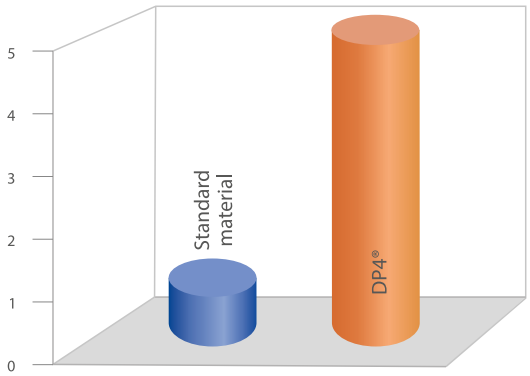

Fig. 12: Relative resistance to cavitation erosion

FLOW EROSION RESISTANCE

The test rig shown in Fig. 13 is designed to reproduce flow erosion damage to the bearing lining of the test specimen.

The test conditions are given in Table 6.

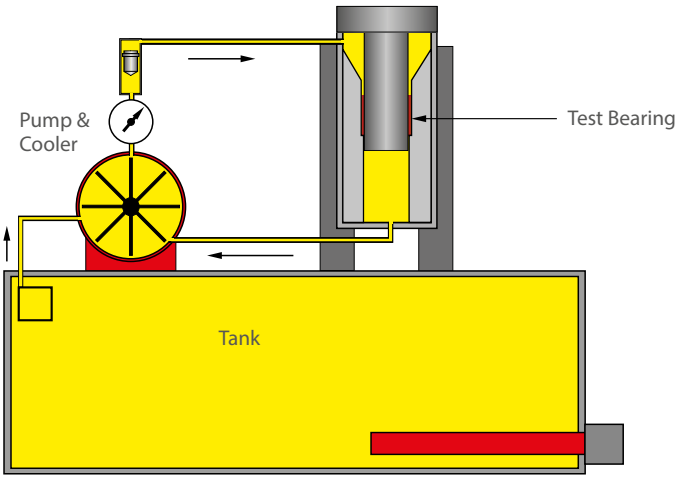

Fig. 13: Principle of the flow erosion test rig

FLOW EROSION - TEST CONDITIONS	
Bearing diameter	20 mm
Bearing length	15 mm
Diametral clearance	0.11 mm
Pressure	13.8 MPa
Flow rate	5 l/min
Test duration	20 hours
Shaft surface finish	0.15 µm ±0.05
Temperature	ambient

Table 6: Flow erosion test conditions

The relative resistance to flow erosion damage of DP4® as evaluated on this test rig is shown in Fig. 14.

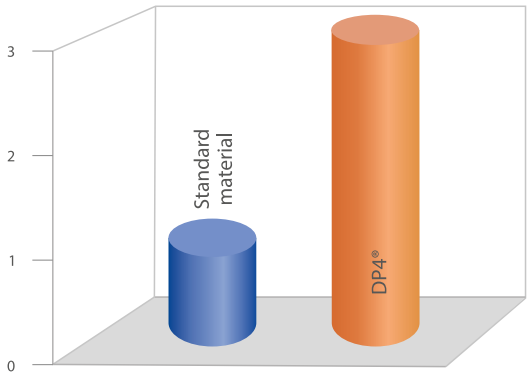

Fig. 14: Relative resistance to flow erosion

4 Bearing Performance

4.2 HYDRAULIC APPLICATIONS

DP4® also shows excellent wear and frictional performance in a wide range of oil lubricated hydraulic applications. The wear resistance of DP4® under steady load oil immersed boundary lubrication conditions has been evaluated using the test rig shown in Fig. 15. The test conditions are given in Table 7.

GGB JUPITER TEST RIG

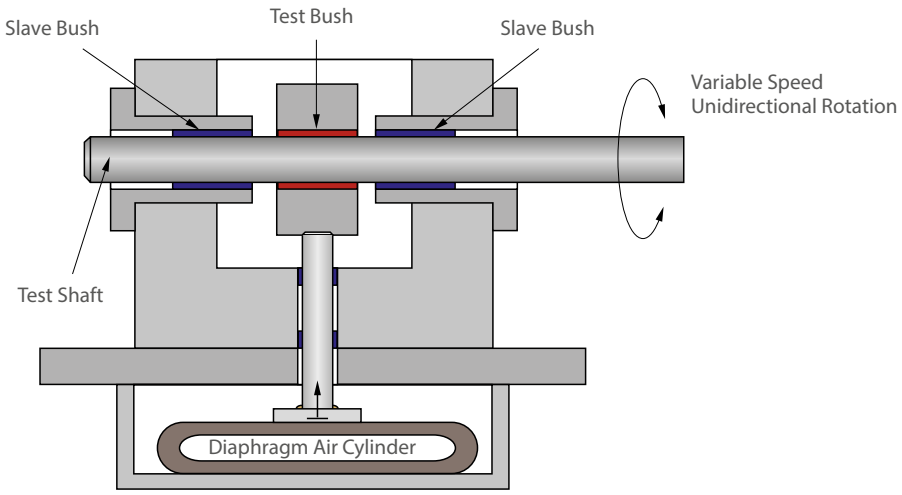

Fig. 15: Principle of the GGB Jupiter test rig

LUBRICATED WEAR - TEST CONDITIONS	
Bearing diameter	20 mm
Bearing length	15 mm
Mean diametral clearance	0.10 mm
Speed	0.11 m/s
Lubricant	ISO VG 46 hydraulic oil

Table 7: Lubricated wear test conditions

The relative PV limits with boundary lubrication of DP4® and the material used in many high performance hydraulic pump applications as determined from these tests are shown in Fig. 16. The limiting PV depends upon the actual operating conditions and hence the relative performance only is given for guidance.

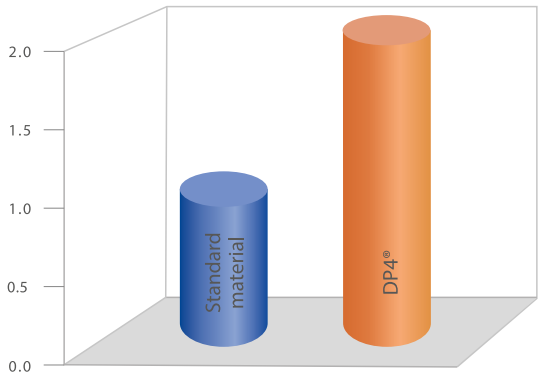

Fig. 16: Relative PU limits

4.3 DRY WEAR PERFORMANCE

DESIGN FACTORS

The main parameters when determining the size or calculating the service life for a DP4® bearing are:

- Specific load limit P_{lim}
- PV Factor
- Mating surface roughness R_a
- Mating surface material
- Temperature T
- Other environmental factors e.g. housing design, dirt, lubricated conditions.

The following calculation can be used to estimate the bearing service life of DP4® under dry running conditions.

SPECIFIC LOAD P

For the purpose of assessing bearing performance the specific load p is defined as the working load divided by the projected area of the bearing and is expressed in MPa.

CYLINDRICAL BUSH

(4.3.1) [MPa]

$$P = \frac{F}{D_i \cdot B}$$

THRUST WASHER

(4.3.2) [MPa]

$$P = \frac{4F}{\pi \cdot (D_o^2 - D_i^2)}$$

FLANGED BUSH (AXIAL LOADING)

(4.3.3) [MPa]

$$P = \frac{F}{0{,}04 \cdot (D_{fl}^2 - D_i^2)}$$

SLIDEWAY

(4.3.4) [MPa]

$$P = \frac{F}{L \cdot W}$$

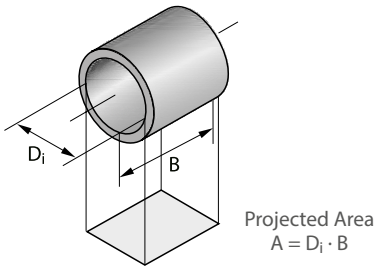

Fig. 17: Projected Area

SPECIFIC LOAD LIMIT P_{lim}

The maximum load which can be applied to a DP4® bearing can be expressed in terms of the Specific Load Limit, which depends on the type of the loading. It is highest under steady loads. Conditions of dynamic load or oscillating movement which produce fatigue stress in the bearing result in a reduction in the permissible Specific Load Limit.

In general the specific load on a DP4® bearing should not exceed the Specific Load Limits given in Table 8.

The values of Specific Load Limit specified in Table 8 assume good alignment between the bearing and mating surface (Fig. 35, page 33).

4 Bearing Performance

MAXIMUM SPECIFIC LOAD P_{lim}

TYPE OF LOADING / P_{lim} [MPa]										
Steady load - rotating movement P_{lim}	140									
Steady load - oscillating movement										
P_{lim}	140	140	115	95	85	80	60	44	30	20
Number of movement cycles Q	1000	2000	4000	6000	8000	10^4	10^5	10^6	10^7	10^8
Dynamic load - rotating or oscillating movement										
P_{lim}	60	60	50	46	42	40	30	22	15	10
Number of load cycles Q	1000	2000	4000	6000	8000	10^4	10^5	10^6	10^7	10^8

Table 8: Maximum specific load P_{lim}

Permanent deformation of the DP4® bearing lining may occur for specific loads above 140 MPa unless with slow intermittent movements. Under these conditions, it is recommended to contact GGB for further information.

The permissible maximum load on a thrust washer is higher than that on the flange of a flanged bush, and under conditions of high axial loads a thrust washer should be specified.

SLIDING SPEED V

Speeds in excess of 2.5 m/s sometimes lead to overheating, and a running in procedure may be beneficial. This could consist of a series of short runs progressively increasing in duration from an initial run of a few seconds.

CONTINUOUS ROTATION

CYLINDRICAL BUSH

(4.3.5) [m/s]

$$V = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3}$$

THRUST WASHER

(4.3.6) [m/s]

$$V = \frac{\frac{D_o + D_i}{2} \cdot \pi \cdot N}{60 \cdot 10^3}$$

OSCILLATING MOVEMENT

CYLINDRICAL BUSH

(4.3.7) [m/s]

$$V = \frac{D_i \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\varphi \cdot N_{OSZ}}{360}$$

THRUST WASHER

(4.3.8) [m/s]

$$V = \frac{\frac{D_o + D_i}{2} \cdot \pi}{60 \cdot 10^3} \cdot \frac{4\varphi \cdot N_{OSZ}}{360}$$



Fig. 18: Oscillating cycle φ

PV FACTOR

The useful operating life of a DP4® bearing is governed by the PV factor, the product of the specific load P [MPa] and the sliding speed V [m/s].

For thrust washers and flanged bush thrust faces the rubbing velocity at the mean diameter is used.

PV factors up to 1.0 MPa x m/s can be accommodated for short periods, whilst for continuous rating, PV factors up to 0.5 MPa x m/s can be used, depending upon the operating life required.

	DU	UNIT
P	140	MPa
V	2.5	m/s
PV continuous	0.5	MPa · m/s
PV intermittent	1.0	MPa · m/s

Table 9: Typical data P, V and PV

CALCULATION OF PU FACTOR

(4.3.9) [MPa · m/s]

$$PV = P \cdot V$$

APPLICATION FACTORS

The following factors influence the bearing performance of DP4® and must be considered in calculating the required dimension or estimating the bearing life for a particular application.

TEMPERATURE

The useful life of a DP4® bearing depends upon the operating temperature.

Under dry running conditions frictional heat is generated at the rubbing surface of the bearing dependent on the PV condition. For a given PV factor the operating temperature of the bearing depends upon the temperature of the surrounding environment, the heat dissipation properties of the housing and the mating surface. Intermittent operation affects the heat dissipation from the assembly and hence the operating temperature of the bearing.

The effect of temperature on the operating life of DP4® bearings is indicated by the factor a_T shown in Table 10.

MODE OF OPERATION	NATURE OF HOUSING	TEMPERATURE OF BEARING ENVIRONMENT T_{amb} [°C] AND TEMPERATURE APPLICATION FACTOR a_T					
		25	60	100	150	200	280
Dry continuous operation	Average heat dissipating qualities	1.0	0.8	0.6	0.4	0.2	0.1
Dry continuous operation	Light pressings or isolated housing with poor heat dissipating qualities	0.5	0.4	0.3	0.2	0.1	-
Dry continuous operation	Non-metallic housings with bad heat dissipating qualities	0.3	0.3	0.2	0.1	-	-
Dry intermittent operation (duration less than 2 min, followed by a longer dwell period)	Average heat dissipating qualities	2.0	1.6	1.2	0.8	0.4	0.2

Table 10: Temperature application factor a_T

4 Bearing Performance

MATING SURFACE

The effect of the mating surface material type on the operating life of DP4® bearings is indicated by the mating surface factor a_M and the life correction constant aL shown in Table 11.

MATERIAL	a_M	a_L
STEEL AND CAST IRON		
Carbon Steel	1	400
Carbon Manganese Steel	1	400
Alloy Steel	1	400
Case Hardened Steel	1	400
Nitrided Steel	1	400
Salt bath nitrocarburised	1	400
Stainless Steel (7-10% Ni, 17-20% Cr)	2	400
Cast Iron (0.3 ± 0.1 µm R_a)	1	400

Table 11: Mating surface factor a_M and life correction constant a_L

NOTE:

The factor values given assume a mating surface finish of $R_a = 0.4 \pm 0.1$ µm.

- A ground surface is preferred to fine turned
- Surfaces should be cleaned of abrasive particles after polishing
- Cast iron surfaces should be ground to Ra = 0.3 ± 0.1 µm
- The grinding cut should be in the same direction as the bearing motion relative to the shaft

BEARING SIZE

The running clearance of a DP4® bearing increases with bearing diameter resulting in a proportionally smaller contact area between the shaft and bearing. This reduction in contact area has the effect of increasing the actual unit load and hence PU factor. The bearing size factor (Fig. 20) is used in the design calculations to allow for this effect.

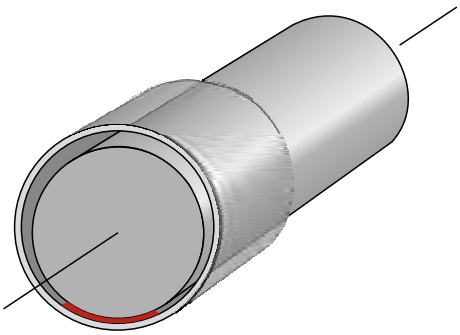

Fig. 19: Contact area between bearing and shaft

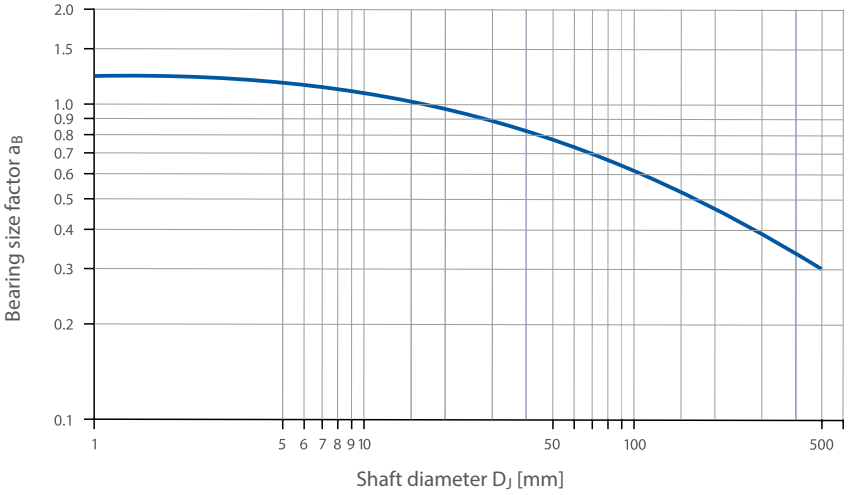

Fig. 20: Bearing size factor a_B

BORE BURNISHING

Burnishing or machining the bore of a DP4® bearing results in a reduction in the wear performance. The application factor a_C given in Table 12 is used in the design calculations to allow for this effect. Machining DP4® is not recommended.

DEGREE OF SIZING		APPLICATION FACTOR a_C
BURNISHING	0.025 mm	0.8
Excess of burnishing tool diameter over	0.038 mm	0.6
mean bore size	0.050 mm	0.3

Table 12: Bore burnishing or machining application factor a_C

TYPE OF LOAD

The type of load is considered in formula (4.4.9) page 23 and (4.4.10) page 23.

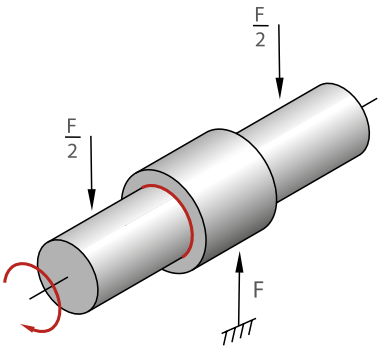

Fig. 21: Steady load, bush stationary, shaft rotating

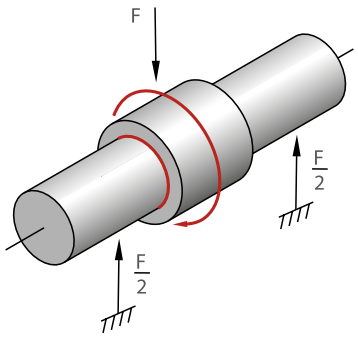

Fig. 22: Rotating load, shaft stationary, bush rotating

4 Bearing Performance

4.4CALCULATION OF BEARING SERVICE LIFE

Where the size of a bearing is governed largely by the space available the following calculation can be used to determine whether its useful life will satisfy the requirements. If the calculated life is inadequate, a larger bearing should be considered.

SPECIFIC LOAD P

BUSHES

(4.4.1) [MPa]

$$P = \frac{F}{D_i \cdot B}$$

FLANGED BUSHES

(4.4.2) [MPa]

$$P = \frac{F}{0.04 \cdot (D_{fl}^2 - D_i^2)}$$

THRUST WASHERS

(4.4.3) [MPa]

$$P = \frac{4F}{P \cdot (D_o^2 - D_i^2)}$$

HIGH LOAD FACTOR a_E

(4.4.4) [-]

$$a_E = \frac{P_{lim} - P}{P_{lim}}$$

If a_E is negative then the bearing is overloaded.
Increase the bearing diameter and/or length.

BUSHES

(4.4.5) [MPa · m/s]

$$PV = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B}$$

FLANGED BUSHES

(4.4.6) [MPa · m/s]

$$PV = \frac{6.5 \cdot 10^{-4} F \cdot N}{a_E \cdot (D_{fl} - D_i) \cdot a_T \cdot a_M \cdot a_B}$$

THRUST WASHERS

(4.4.7) [MPa · m/s]

$$PV = \frac{3.34 \cdot 10^{-5} F \cdot N}{a_E \cdot (D_o - D_i) \cdot a_T \cdot a_M \cdot a_B}$$

For oscillating movement, calculate the average rotational speed.

(4.4.8) [1/min]

$$N = \frac{4\varphi \cdot N_{osz}}{360}$$



Fig. 23: Oscillating cycle φ

ESTIMATION OF BEARING LIFE L_H

BUSHES (STEADY LOAD)

(4.4.9) [h]

$$L_H = \frac{265}{PV} - a_L$$

BUSHES (ROTATING LOAD)

(4.4.10) [h]

$$L_H = \frac{530}{PV} - a_L$$

FLANGED BUSHES (AXIAL LOAD)

(4.4.11) [h]

$$L_H = \frac{175}{PV} - a_L$$

THRUST WASHERS

(4.4.12) [h]

$$L_H = \frac{175}{PV} - a_L$$

BORE BURNISHING

If the DP4® bush is bore burnished then this must be allowed for in estimating the bearing life by the application factor a_C (Table 12, page 21).

ESTIMATED BEARING LIFE

(4.4.13) [h]

$$L_H = L_H \cdot a_C$$

FOR OSCILLATING MOVEMENTS OR DYNAMIC LOADS

(4.4.14) [cycles]

$$Z_T = L_H \cdot N_{OSC} \cdot 60$$

for oscillating movements

(4.4.15) [cycles]

$$Z_T = L_H \cdot C \cdot 60$$

for dynamic loads

Calculate estimated number of cycles Z_T

Check that Z_T is less than total number of cycles Q for the operating specific load P (Table 8, page 18)

If $Z_T < Q$, L_H will be limited by wear after Z_T cycles.

If $Z_T > Q$, L_H will be limited by fatigue after Z_T cycles.

SLIDEWAYS

SPECIFIC LOAD FACTOR

(4.4.16) [-]

$$a_{E1} = A - \frac{F}{P_{lim}}$$

If negative the bearing is overloaded and the bearing area should be increased.

SPEED TEMPERATURE AND MATERIAL APPLICATION FACTORS

(4.4.17) [-]

$$a_{E2} = \frac{280 \cdot a_T \cdot a_M}{F \cdot V}$$

RELATIVE CONTACT AREA FACTOR

(4.4.18) [-]

$$a_{E3} = \frac{A}{A_M}$$

ESTIMATED BEARING LIFE

(4.4.19) [-]

$$L_H = a_{E1} \cdot a_{E2} \cdot a_{E3} - a_L$$

NOTE:
Estimated bearing lives greater than 4000 h are subject to error due to inaccuracies in the extrapolation of test data.

4 Bearing Performance

4.5 WORKED EXAMPLES

CYLINDRICAL BUSH

Given:			
Load Details	Steady Load Continuous Rotation	Inside Diameter D_i Length B	40 mm 30 mm
Shaft	Steel Unlubricated at 25°C	Bearing Load F Rotational Speed N	5.000 N 25 · 1/min

Calculation Constants and Application Factors		
Specific Load Limit P_{lim}	140 MPa	(Table 8, page 18)
Temperature Application Factor a_T	1.0	(Table 10, page 19)
Material Application Factor a_M	1.0	(Table 11, page 20)
Bearing Size Factor a_B	0.85	(Fig. 20, page 21)
Life Correction Constant a_L	400	(Table 11, page 20)

Calculation	Ref	Value
Specific Load P [MPa]	(4.4.1) Page 22	$P = \frac{F}{D_i \cdot B} = \frac{5.000}{40 \cdot 30} = 4.17$
Sliding Speed V [m/s]	(4.3.5) Page 18	$V = \frac{D_i \cdot \pi \cdot N}{60 \cdot 10^3} = \frac{40 \cdot 3.14 \cdot 25}{60 \cdot 10^3} = 0.052$
High Load Factor a_E [-] must be > 0	(4.4.4) Page 22	$a_E = \frac{P_{lim} - P}{P_{lim}} = \frac{140 - 4.17}{140} = 0.97$
Modified PV Factor [MPa · m/s]	(4.4.5) Page 22	$PV = \frac{5.25 \cdot 10^{-5} F \cdot N}{a_E \cdot B \cdot a_T \cdot a_M \cdot a_B} = 0.27$
Life L_H [h]	(4.4.9) Page 23	$L_H = \frac{265}{PU} - a_L = \frac{265}{0.27} - 400 = 581$

FLANGED BUSH

Given:			
Load Details	Axial Load Continuous Rotation	Flange Outside Ø D_{fl} Inside Diameter D_i	23 mm 15 mm
Shaft	Steel Unlubricated at 25°C	Bearing Load F Rotational Speed N	250 N 5 · 1/min

Calculation Constants and Application Factors		
Specific Load Limit P_{lim}	140 MPa	(Table 8, page 18)
Temperature Application Factor a_T	1.0	(Table 10, page 19)
Material Application Factor a_M	1.0	(Table 11, page 20)
Bearing Size Factor a_B	1.0	(Fig. 20, page 21)
Life Correction Constant a_L	400	(Table 11, page 20)

Calculation	Ref	Value
Specific Load P [N/mm²]	(4.4.2) Page 22	$P = \frac{250}{0.04 \cdot (23^2 - 15^2)} = 20.55$
Sliding Speed V [m/s]	(4.3.6) Page 18	$V = \frac{\frac{23 + 15}{2} \cdot 3{,}14 \cdot 5}{60 \cdot 10^3} = 0.005$
High Load Factor a_E [-] must be > 0	(4.4.4) Page 22	$a_E = \frac{P_{lim} - P}{P_{lim}} = \frac{140 - 20.55}{140} = 0.835$
Modified PV Factor [N/mm² · m/s]	(4.4.6) Page 22	$PV = \frac{6.5 \cdot 10^{-4} \cdot 250 \cdot 5}{0.853 \cdot (23 - 15) \cdot 1 \cdot 1 \cdot 1} = 0{,}119$
Life L_H [h]	(3.8.11) Page 21	$L_H = \frac{175}{PU} - a_L = \frac{175}{0.119} - 400 = 1071$

THRUST WASHER

Given:			
Load Details	Axial Load Continuous Rotation	Outside Diameter D_o Inside Diameter D_i	62 mm 38 mm
Shaft	Steel Unlubricated at 25°C	Bearing Load F Rotational Speed N	6.500 N 10 · 1/min

Calculation Constants and Application Factors		
Specific Load Limit P_{lim}	140 MPa	(Table 8, page 18)
Temperature Application Factor a_T	1.0	(Table 10, page 19)
Material Application Factor a_M	1.0	(Table 11, page 20)
Bearing Size Factor a_B	0.85	(Fig. 20, page 21)
Life Correction Constant a_L	400	(Table 11, page 20)

Calculation	Ref	Value
Specific Load P [N/mm²]	(4.4.3) Page 22	$P = \frac{4 \cdot 6.500}{3.14 \cdot (62^2 - 38^2)} = 3.45$
Sliding Speed V [m/s]	(4.3.6) Page 18	$V = \frac{\frac{62 + 38}{2} \cdot 3{,}14 \cdot 10}{60 \cdot 10^3} = 0.026$
High Load Factor a_E [-] must be > 0	(4.4.4) Page 22	$a_E = \frac{P_{lim} - P}{P_{lim}} = \frac{140 - 3.45}{140} = 0.975$
Modified PV Factor [MPa · m/s]	(4.4.7) Page 22	$PV = \frac{3.34 \cdot 10^{-5} \cdot 6.500 \cdot 10}{0.975 \cdot (62 - 38) \cdot 1 \cdot 1 \cdot 0.85} = 0.11$
Life L_H [h]	(4.4.12) Page 23	$L_H = \frac{175}{PU} - a_L = \frac{175}{0.11} - 400 = 1191$

5 Lubrication

DP4® provides excellent performance in lubricated applications. The following sections describe the basics of lubrication and provide guidance on the application of DP4® in such environments.

5.1 LUBRICANTS

DP4® can be used with most fluids including:

- water
- lubricating oils
- engine oil
- turbine oil
- hydraulic fluid
- solvent
- refrigerants

In general, the fluid will be acceptable if it does not chemically attack the PTFE/lead overlay or the porous bronze interlayer. Where there is doubt about the suitability of a fluid, a simple test is to submerge a sample of DP4® material in the fluid for two to three weeks at 15-20 °C above the operating temperature.

The following will usually indicate that the fluid is not suitable for use with DP4®:

- A significant change in the thickness of the DP4® material,
- a visible change in the bearing surface other than some discolouration or staining,
- a visible change in the microstructure of the bronze interlayer.

5.2 TRIBOLOGY

There are three modes of lubricated bearing operation which relate to the thickness of the developed lubricant film between the bearing and the mating surface.

- Hydrodynamic lubrication
- Mixed film lubrication
- Boundary lubrication

These three modes of operation depend upon:

- Bearing dimensions
- Clearance
- Load
- Speed
- Lubricant Viscosity
- Lubricant Flow

HYDRODYNAMIC LUBRICATION

CHARACTERISED BY:

- Complete separation of the shaft from the bearing by the lubricant film
- Very low friction and no wear of the bearing or shaft since there is no contact.
- Coefficients of friction of 0.001 to 0.01

Hydrodynamic conditions occur when:

(5.2.1) [MPa]

$$P \leq \frac{V \cdot \eta}{7.5} \cdot \frac{B}{D_i}$$

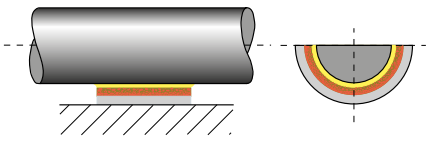

Fig. 24: Hydrodynamic lubrication

5 Lubrication

MIXED FILM LUBRICATION

CHARACTERISED BY:

- Combination of hydrodynamic and boundary lubrication.
- Part of the load is carried by localised areas of self pressurised lubricant and the remainder supported by boundary lubrication.
- Friction and wear depend upon the degree of hydrodynamic support developed.
- DP4® provides low friction and high wear resistance to support the boundary lubricated element of the load.

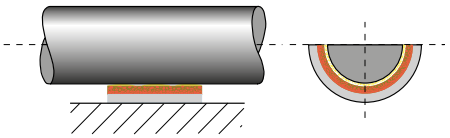

Fig. 25: Mixed film lubrication

BOUNDARY LUBRICATION

CHARACTERISED BY:

- Rubbing of the shaft against the bearing with virtually no lubricant separating the two surfaces.
- Bearing material selection is critical to performance
- Shaft wear is likely due to contact between bearing and shaft.
- The excellent self lubricating properties of DP4® material minimises wear under these conditions.
- The dynamic coefficient of friction with DP4® is typically 0.05 to 0.3 under boundary lubrication conditions.
- The static coefficient of friction with DP4® is typically slightly above the dynamic coefficient of friction under boundary lubrication conditions.

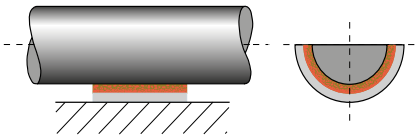

Fig. 26: Boundary lubrication

5.3 CHARACTERISTICS OF LUBRICATED DP4® BEARINGS

DP4® is particularly effective in the most demanding of lubricated applications where full hydrodynamic operation cannot be maintained, for example:

- **High load conditions**

  In highly loaded applications operating under boundary or mixed film conditions DP4® shows excellent wear resistance and low friction.

- **Start up and shut down under load**

  With insufficient speed to generate a hydrodynamic film the bearing will operate under boundary or mixed film conditions. DP4® minimises wear and requires less start up torque than conventional metallic bearings.

- **Sparse lubrication**

  Many applications require the bearing to operate with less than the ideal lubricant supply, typically with splash or mist lubrication only. DP4® requires significantly less lubricant than conventional metallic bearings.

- **Non lubricating fluids**

  DP4® operates satisfactorily in low viscosity and non lubricating fluids such as water and some process fluids.

NOTE THE FOLLOWING HOWEVER:

If a DP4® bearing is required to run dry after running in water under non hydrodynamic conditions then the wear resistance will be substantially reduced due to an increased amount of bedding in wear.

Fig. 27, page 28 shows the three lubrication regimes discussed above plotted on a graph of sliding speed vs the ratio of specific load to lubricant viscosity.

Using the formula in Section 4:

- Calculate the specific load P,
- Calculate the shaft surface speed V.

Using the viscosity temperature relationships presented in Table 13:

- Determine the viscosity in centipoise of the lubricant.

Note:
Viscosity is a function of operating temperature. If the operating temperature of the fluid is unknown, a provisional temperature of 25 °C above ambient can be used.

VISCOSITY η [cP]															
TEMPERATURE [°C]	0	10	20	30	40	50	60	70	80	90	100	110	120	130	140
Lubricant															
ISO VG 32	310	146	77	44	27	18	13	9.3	7.0	5.5	4.4	3.6	3.0	2.5	2.2
ISO VG 46	570	247	121	67	40	25	17	12	9.0	6.9	5.4	4.4	3.6	3.0	2.6
ISO VG 68	940	395	190	102	59	37	24	17	12	9.3	7.2	5.8	4.7	3.9	3.3
ISO VG 100	2110	780	335	164	89	52	33	22	15	11.3	8.6	6.7	5.3	4.3	3.6
ISO VG 150	3600	1290	540	255	134	77	48	31	21	15	11	8.8	7.0	5.6	4.6
Diesel oil	4.6	4.0	3.4	3.0	2.6	2.3	2.0	1.7	1.4	1.1	0.95				
Petrol	0.6	0.56	0.52	0.48	0.44	0.40	0.36	0.33	0.31						
Kerosene	2.0	1.7	1.5	1.3	1.1	0.95	0.85	0.75	0.65	0.60	0.55				
Water	1.79	1.30	1.0	0.84	0.69	0.55	0.48	0.41	0.34	0.32	0.28				

Table 13: Dynamic viscosity

5 Lubrication

5.4 DESIGN GUIDANCE

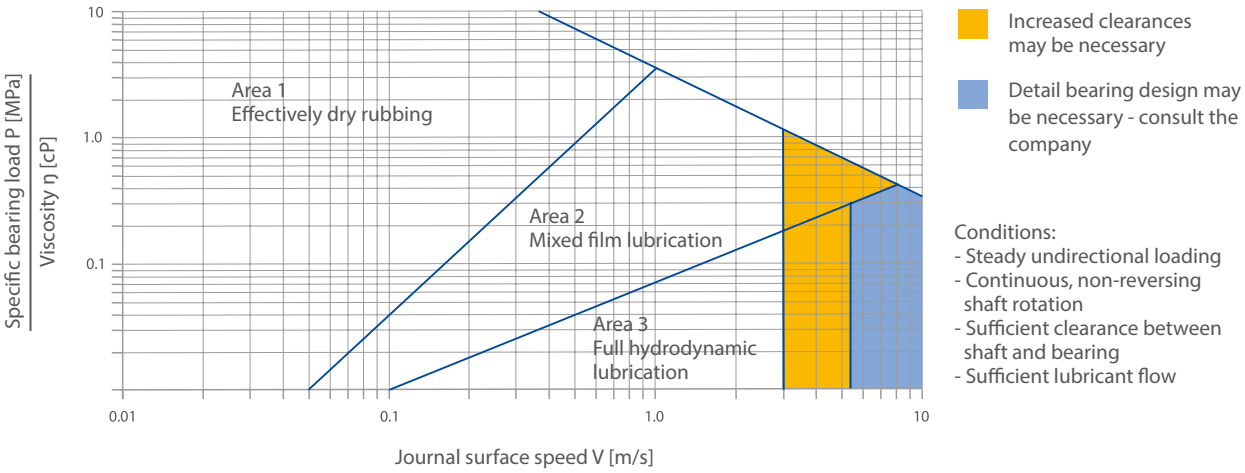

Fig. 27: Design guide for lubricated application

EXPLANATION TO FIGURE 27

AREA 1

The bearing will operate with boundary lubrication and PV factor will be the major determinant of bearing life. The DP4® bearing performance can be calculated using the method given in section 4, although the result will probably underestimate the bearing life

AREA 2

The bearing will operate with mixed film lubrication and the PV factor is no longer a significant parameter in determining the bearing life. The DP4® bearing performance will depend upon the nature of the fluid and the actual service conditions.

AREA 3

The bearing will operate with hydrodynamic lubrication. The bearing wear will be determined only by the cleanliness of the lubricant and the frequency of start up and shut down.

AREA 4

These are the most demanding operating conditions. The bearing is operated under either high speed or high bearing load to viscosity ratio, or a combination of both. These conditions may cause:

- excessive operating temperature and/or
- high wear rate.

The bearing performance may be improved by adding one or more grooves to the bearing and a shaft surface finish <0.05 µm R_a.

5.5 CLEARANCES FOR LUBRICATED OPERATION

The recommended shaft and housing diameters given for standard DP4® bushes will provide sufficient clearance for applications operating with boundary lubrication.

For bearings operating with mixed film or hydrodynamic lubrication it may be necessary to improve the fluid flow through the bearing by reducing the recommended shaft diameter by approximately 0.1 %, particularly when the shaft surface speed exceeds 2.5 m/s.

5.6 GROOVING FOR LUBRICATED OPERATION

In demanding applications an axial oil groove will improve the performance of DP4®. Figure 28 shows the recommended form and location of a single groove with respect to the applied load and the bearing split. GGB can manufacture special DP4® bearings with embossed or milled grooves on request.

5.7 MATING SURFACE FINISH FOR LUBRICATED OPERATION

- $R_a \leq 0.4 \pm 0.1$ µm boundary lubrication
- $R_a = 0.1$ - 0.2 µm mixed film or hydrodynamic conditions
- $R_a \leq 0.05$ µm for the most demanding operating conditions

5.8 GREASE LUBRICATION

DP4® is not generally recommended for use with grease lubrication. In particular the following must be avoided:

- Dynamic loads - which can result in erosion of the PTFE/lead bearing surface.
- Greases with EP additives or fillers such as graphite or MoS_2 which can cause rapid wear of DP4®.

Under grease lubrication, improved performance can be obtained by the use of other GGB metal polymer bearing materials, for example, DX®, DX®10, DS, HI-EX®.

Please contact your local sales representative or consult: **https://www.ggbearings.com** for more details.

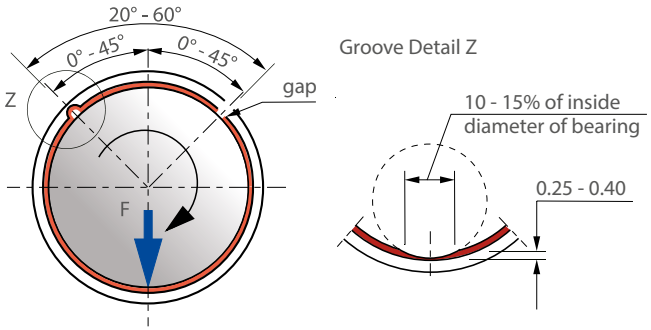

Fig. 28: Location of oil holes and grooves

6 Bearing Assembly

DIMENSIONS AND TOLERANCES

DP4® bushes are prefinished and excluding very exceptional circumstances, must not be broached, machined or otherwise modified in the bore. It is essential that the correct running clearance is used and that both the diameter of the shaft and the bore of the housing are finished to the limits given in the tables. Under dry running conditions any increase in the clearances given will result in a proportional reduction in performance.

If the bearing housing is unusually flexible the bush will not close in by the calculated amount and the running clearance will be more than the optimum. In these circumstances the housing should be bored slightly undersize or the journal diameter increased, the correct size being determined by experiment.

Where free running is essential, or where light loads (less than 0.1 MPa) prevail and the available torque is low, increased clearance is required and it is recommended that the shaft size quoted in the table be reduced by 0.025 mm.

6.1 ALLOWANCE FOR THERMAL EXPANSION

For operation in high temperature environments the clearance should be increased by the amounts indicated by figure 29 to compensate for the inward thermal expansion of the bearing lining.

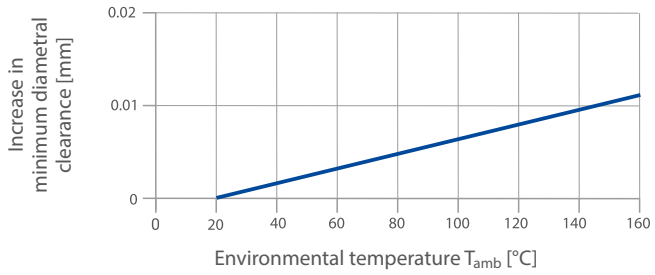

Fig. 29: Increase in diametral clearance

If the housing is non-ferrous then the bore should be reduced by the amounts given in Table 14, in order to give an increased interference fit to the bush, with a similar reduction in the journal diameter additional to that indicated by figure 29.

HOUSING MATERIAL	REDUCTION IN HOUSING DIAMETER PER 100°C RISE	REDUCTION IN SHAFT DIAMETER PER100°C RISE
Aluminium alloys	0.1 %	0.1 % + values from Fig.29
Copper base alloys	0.05 %	0.05 % + values from Fig.29
Steel and cast iron	–	values from Fig.29
Zinc base alloys	0.15 %	0.15 % + values from Fig.29

Table 14: Allowance for high temperature

6.2 TOLERANCES FOR MINIMUM CLEARANCE

Where it is required to keep the variation of assembled clearance to a minimum, closer tolerances can be specified towards the upper end of the journal tolerance and the lower end of the housing tolerance. If housings to H6 tolerance are used, then the journals should be finished to the following limits. The sizes in Table 16 give the following nominal clearance range.

D_i	D_J
> 5 mm < 25 mm	-0.019 to -0.029
> 25 mm < 50 mm	-0.021 to -0.035

Table 15: Shaft tolerances for use with H6 housings

D_i	D_J
10 mm	0.009 to 0.080
50 mm	0.011 to 0.134

Table 16: Clearance vs bearing diameter

BURNISHING

The burnishing or fine boring of the bore of an assembled DP4® bush in order to achieve a smaller clearance tolerance is only permissible if a substantial reduction in performance is acceptable. Fig. 24 shows a recommended burnishing tool for the sizing of DP4® bushes.

The coining section of the burnishing tool should be case hardened (case depth 0.6 - 1.2 mm, HRC 60±2) and polished with diamond paste ($R_Z \approx 1$ µm). A TiN type surface treatment increases the wear resistance of the burnishing tool and when absent gives a visual indication of burnishing tool wear.

Note: Ball burnishing of DP4® bushes is not recommended.

The values given in Table 17 indicate the dimensions of the burnishing tool required to give specific increases in the bearing bore diameter.

Exact values must be determined by test.

The reduction in bearing performance as a result of burnishing is allowed for in the bearing life calculation by the application factor a_C (Table 12, page 21). The impact of burnishing on the bearing and assembly should be validated by trials.

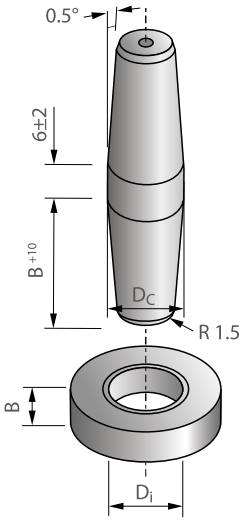

Fig. 30: Burnishing tool

ASSEMBLED BUSH INSIDE Ø	REQUIRED BUSH INSIDE Ø	REQUIRED BURNISHING TOOL Ø DC
$D_{i,a}$	$D_{i,a}$ + 0.025	$D_{i,a}$ + 0.06
$D_{i,a}$	$D_{i,a}$ + 0.038	$D_{i,a}$ + 0.08
$D_{i,a}$	$D_{i,a}$ + 0.050	$D_{i,a}$ + 0.1

Table 17: Burnishing tool tolerances

6.3 COUNTERFACE DESIGN

The suitability of mating surface materials and recommendations of mating surface finish for use with DP4® are discussed in detail on page 20.

DP4® is normally used in conjunction with ferrous journals and thrust faces, but in damp or corrosive surroundings, particularly without the protection of oil or grease, stainless steel, hard chromium plated mild steel, or hard anodised aluminium is recommended. When plated mating surfaces are specified the plating should possess adequate strength and adhesion, particularly if the bearing is to operate with high fluctuating loads.

The shaft or thrust collar used in conjunction with the DP4® bush or thrust washer must extend beyond the bearing surface in order to avoid cutting into it. The mating surface must also be free from grooves or flats, the end of the shaft should be given a lead-in chamfer and all sharp edges or projections which may damage the soft overlay of the DP4® must be removed.

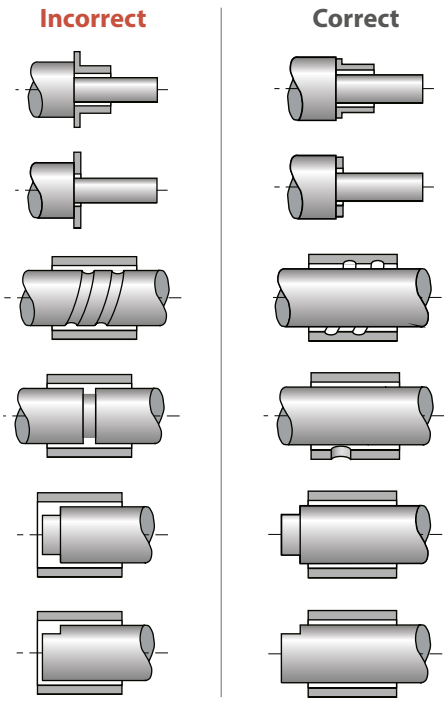

Fig. 31: Counterface Design

6 Bearing Assembly

6.4 INSTALLATION

FITTING OF CYLINDRICAL BUSHES

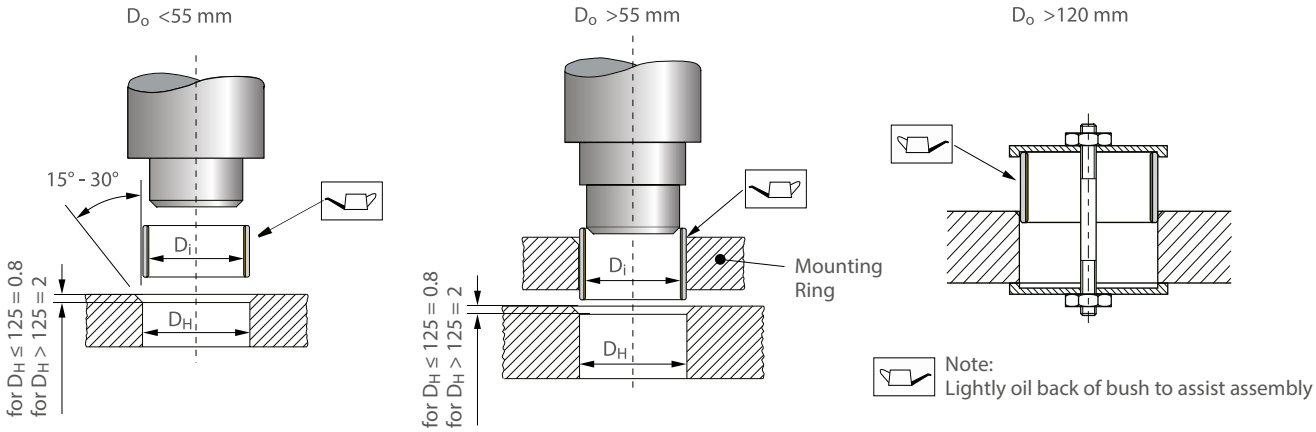

Fig. 32: Fitting of cylindrical bushes

FITTING OF FLANGED BUSHES

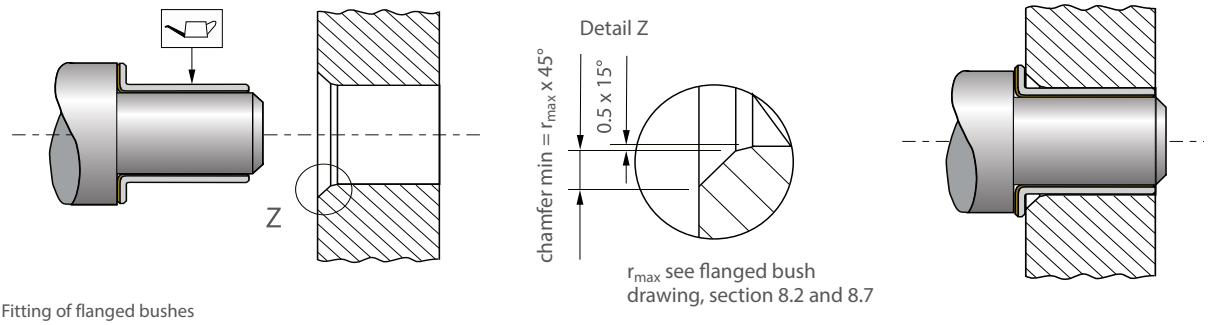

Fig. 33: Fitting of flanged bushes

INSERTION FORCES

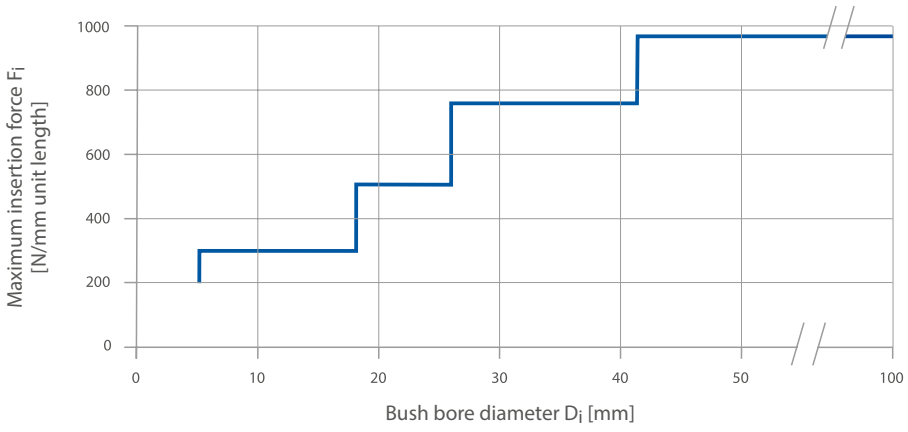

Fig. 34: Maximum Insertion Force F_i

ALIGNMENT

Accurate alignment is an important consideration for all bearing assemblies, but is particularly so for dry bearings because there is no lubricant to spread the load. With DP4® bearings misalignment over the length of a bush (or pair of bushes), or over the diameter of a thrust washer should not exceed 0.020 mm as illustrated in Fig. 35.

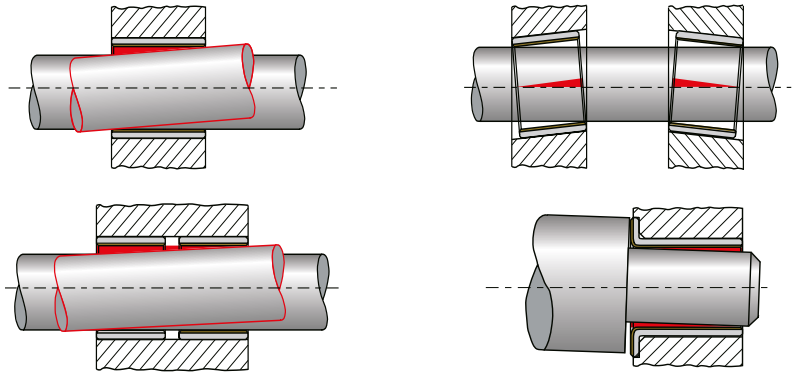

Fig. 35: Alignment

SEALING

While DP4® can tolerate the ingress of some contaminant materials into the bearing without loss of performance, where there is the possibility of highly abrasive material entering the bearing, a suitable sealing arrangement, as illustrated in Fig. 36 should be provided.

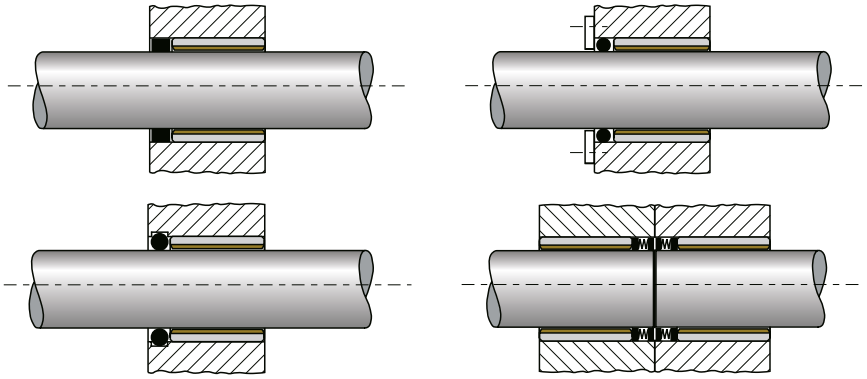

Fig. 36: Recommended sealing arrangements

6.5 AXIAL LOCATION

Where axial location is necessary, it is advisable to fit DP4® thrust washers in conjunction with DP4® bushes, even when the axial loads are low.

FITTING OF THRUST WASHERS

DP4® thrust washers should be located in a recess as shown in Fig. 37. For the recess diameter the tolerance class [D10] is recommended. The recess depth is given in the product tables, page 44 and following. If a recess is not possible one of the following methods may be used:

– Two dowel pins – Two screws – Adhesive – Soldering (temperature < 320 °C).

6 Bearing Assembly

IMPORTANT NOTE

- Ensure the washer ID does not touch the shaft after assembly
- Ensure that the washer is mounted with the steel backing to the housing
- Dowels pins should be recessed 0.25 mm below the bearing surface
- Screws should be countersunk 0.25 mm below the bearing surface
- DP4® must not be heated above 320 °C
- Contact adhesive manufacturers for guidance selection of suitable adhesive
- Protect the bearing surface to prevent contact with adhesive

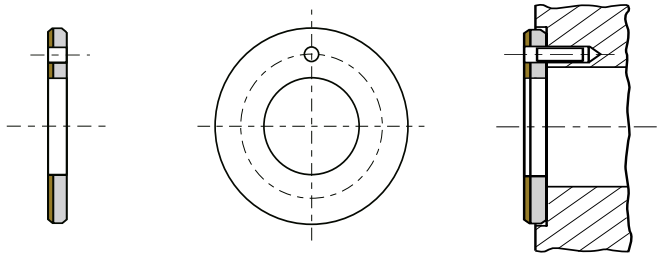

Fig. 37: Installation of Thrust Washer

GROOVES FOR WEAR DEBRIS REMOVAL

Tests with thrust washers have demonstrated that for optimum dry wear performance at specific loads in excess of 35 MPa, four wear debris removal grooves should be machined in the bearing surface as shown in Fig. 38.

Grooves in bushes have not been found to be beneficial in this respect.

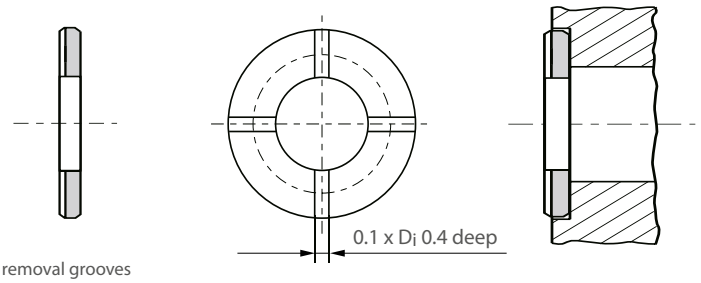

Fig. 38: Debris removal grooves

SLIDEWAYS

DP4® strip material for use as slideway bearings should be installed using one of the following methods:

- Countersunk screws
- Adhesives
- Mechanical location as shown in Fig. 39

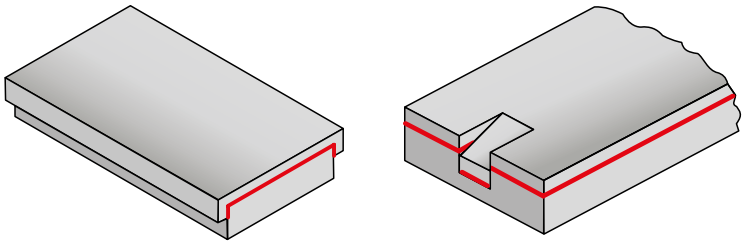

Fig. 39: Mechanical location of DU slideplates

7 Modification

7.1 CUTTING AND MACHINING

The modification of DP4® bearing components requires no special procedures. In general it is more satisfactory to perform machining or drilling operations from the PTFE side in order to avoid burrs. When cutting is done from the steel side, the minimum cutting pressure should be used and care taken to ensure that any steel or bronze particles protruding into the remaining bearing material, and all burrs, are removed.

DRILLING OIL HOLES

Bushes should be adequately supported during the drilling operation to ensure that no distortion is caused by the drilling pressure.

CUTTING PLATE MATERIAL

DP4® plate material may be cut to size by any one of the following methods:

- Using side and face cutter, or slitting saw, with the strip held flat and securely on a horizontal milling machine
- Cropping
- Guillotine (for widths less than 90 mm only)
- Water-jet cutting
- Laser cutting (see Health Warning)

Care must be taken to protect the bearing surface from damage and to ensure that no deformation of the strip occurs.

7.2 ELECTROPLATING

DP4® COMPONENTS

In order to provide some protection in mildly corrosive environments the steel back and end faces of standard range DP4® bearings are tin flashed.

DP4® can be electroplated with most of the conventional electroplating metals including the following:

- zinc ISO 2081
- nickel ISO 1456
- hard chromium ISO 1456

For the harder materials if the specified plating thickness exceeds approximately 5 µm then the housing diameter should be increased by twice the plating thickness in order to maintain the correct assembled bearing bore size.

Where electrolytic attack is possible tests should be conducted to ensure that all the materials in the bearing environment are mutually compatible.

8 Standard Products

8.1 DP4® CYLINDRICAL BUSHES - metric sizes



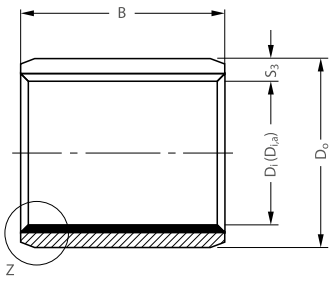

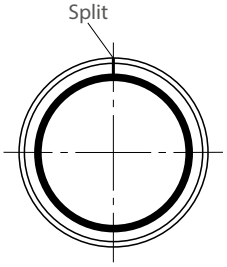

Dimensions and Tolerances according to ISO 3547 and GGB Specifications

OUTSIDE C_o AND INSIDE C_i CHAMFERS

WALL THICKNESS S_3	C_o (a) MACHINED	/ ROLLED	C_i (b)
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5

WALL THICKNESS S_3	C_o (a) MACHINED	/ ROLLED	C_i (b)
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

(a) = chamfer C_o machined or rolled at the option of the manufacturer
(b) = C_i can be a radius or a chamfer in accordance with ISO 13715

PART NO.	NOMINAL DIAMETER D_i	D_o	WALL THICKNESS S_3 max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
0203DP4	2	3.5	0.750 0.730	3.25 2.75	h6	2.000 1.994	H6	3.508 3.500	2.048 2.000	0.054 0.000
0205DP4				5.25 4.75						
0303DP4	3	4.5		3.25 2.75		3.000 2.994		4.508 4.500	3.048 3.000	
0305DP4				5.25 4.75						
0306DP4				6.25 5.75						
0403DP4	4	5.5		3.25 2.75		4.000 3.992		5.508 5.500	4.048 4.000	0.056 0.000
0404DP4				4.25 3.75						
0406DP4				6.25 5.75						
0410DP4				10.25 9.75						
0505DP4	5	7	1.005 0.980	5.25 4.75	f7	4.990 4.978	H7	7.015 7.000	5.055 4.990	0.077 0.000
0508DP4				8.25 7.75						
0510DP4				10.25 9.75						
0604DP4	6	8		4.25 3.75		5.990 5.978		8.015 8.000	6.055 5.990	
0606DP4				6.25 5.75						
0608DP4				8.25 7.75						
0610DP4				10.25 9.75						
0705DP4	7	9		5.25 4.75		6.987 6.972		9.015 9.000	7.055 6.990	0.083 0.003
0710DP4				10.25 9.75						

All dimensions in mm

PART NO.	NOMINAL DIAMETER D_i	NOMINAL DIAMETER D_o	WALL THICKNESS S_3 max. min.	WIDTH B max. min.		SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
0806DP4	8	10	1.005 0.980	6.25 5.75	f7	7.987 7.972	H7	10.015 10.000		8.055 7.990	0.083 0.003
0808DP4				8.25 7.75							
0810DP4				10.25 9.75							
0812DP4				12.25 11.75							
1006DP4	10	12		12.25 11.75		9.987 9.972		12.018 12.000		10.058 9.990	0.086 0.003
1008DP4				8.25 7.75							
1010DP4				10.25 9.75							
1012DP4				12.25 11.75							
1015DP4				15.25 14.75							
1020DP4				20.25 19.75							
1208DP4	12	14		8.25 7.75		11.984 11.966		14.018 14.000		12.058 11.990	0.092 0.006
1210DP4				10.25 9.75							
1212DP4				12.25 11.75							
1215DP4				15.25 14.75							
1220DP4				20.25 19.75							
1225DP4				25.25 24.75							
1310DP4	13	15		10.25 9.75		12.984 12.966		15.018 15.000		13.058 12.990	
1320DP4				20.25 19.75							
1405DP4	14	16		5.25 4.75		13.984 13.966		16.018 16.000		14.058 13.990	
1410DP4				10.25 9.75							
1412DP4				12.25 11.75							
1415DP4				15.25 14.75							
1420DP4				20.25 19.75							
1425DP4				25.25 24.75							
1510DP4	15	17		10.25 9.75		14.984 14.966		17.018 17.000		15.058 14.990	
1512DP4				12.25 11.75							
1515DP4				15.25 14.75							
1520DP4				20.25 19.75							
1525DP4				25.25 24.75							
1610DP4	16	18		10.25 9.75		15.984 15.966		18.018 18.000		16.058 15.990	
1612DP4				12.25 11.75							
1615DP4				15.25 14.75							
1620DP4				20.25 19.75							
1625DP4				25.25 24.75							
1720DP4	17	19		20.25 19.75		16.984 16.966		19.021 19.000		17.061 16.990	0.095 0.006

All dimensions in mm

8 Standard Products

PART NO.	NOMINAL DIAMETER D_i	NOMINAL DIAMETER D_o	WALL THICKNESS S_3 max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.	HOUSING Ø D_H [H6, H7] max. min.	BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
1810DP4	18	20	1.005 0.980	10.25 9.75	17.984 17.966	20.021 20.000	18.061 17.990	0.095 0.006
1815DP4				15.25 14.75				
1820DP4				20.25 19.75				
1825DP4				25.25 24.75				
2010DP4	20	23	1.505 1.475	10.25 9.75	19.980 19.959	23.021 23.000	20.071 19.990	0.112 0.010
2015DP4				15.25 14.75				
2020DP4				20.25 19.75				
2025DP4				25.25 24.75				
2030DP4				30.25 29.75				
2215DP4	22	25		15.25 14.75	21.980 21.959	25.021 25.000	22.071 21.990	
2220DP4				20.25 19.75				
2225DP4				25.25 24.75				
2230DP4				30.25 29.75				
2415DP4	24	27		15.25 14.75	23.980 23.959	27.021 27.000	24.071 23.990	
2420DP4				20.25 19.75				
2425DP4				25.25 24.75				
2430DP4				30.25 29.75				
2515DP4	25	28		15.25 14.75	24.980 24.959	28.021 28.000	25.071 24.990	
2520DP4				20.25 19.75				
2525DP4				25.25 24.75				
2530DP4				30.25 29.75				
2550DP4				50.25 49.75				
2815DP4	28	32	2.005 1.970	15.25 14.75	27.980 27.959	32.025 32.000	28.085 27.990	0.126 0.010
2820DP4				20.25 19.75				
2825DP4				25.25 24.75				
2830DP4				30.25 29.75				
3010DP4	30	34		10.25 9.75	29.980 29.959	34.025 34.000	30.085 29.990	
3015DP4				15.25 14.75				
3020DP4				20.25 19.75				
3025DP4				25.25 24.75				
3030DP4				30.25 29.75				
3040DP4				40.25 39.75				
3220DP4	32	36		20.25 19.75	31.975 31.950	36.025 36.000	32.085 31.990	0.135 0.015
3230DP4				30.25 29.75				
3240DP4				40.25 39.75				

f7 | H7

All dimensions in mm

PART NO.	NOMINAL DIAMETER D_i	NOMINAL DIAMETER D_o	WALL THICKNESS S_3 max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
3520DP4	35	39	2.005 1.970	20.25 19.75	f7	34.975 34.950	H7	39.025 39.000	35.085 34.990	0.135 0.015
3530DP4				30.25 29.75						
3535DP4				35.25 34.75						
3540DP4				40.25 39.75						
3550DP4				50.25 49.75						
3720DP4	37	41		20.25 19.75		36.975 36.950		41.025 41.000	37.085 36.990	
4020DP4	40	44		20.25 19.75		39.975 39.950		44.025 44.000	40.085 39.990	
4030DP4				30.25 29.75						
4040DP4				40.25 39.75						
4050DP4				50.25 49.75						
4520DP4	45	50		20.25 19.75		44.975 44.950		50.025 50.000	45.105 44.990	0.155 0.015
4530DP4				30.25 29.75						
4540DP4				40.25 39.75						
4545DP4				45.25 44.75						
4550DP4				50.25 49.75						
5020DP4	50	55		20.25 19.75		49.975 49.950		55.030 55.000	50.110 49.990	0.160 0.015
5030DP4				30.25 29.75						
5040DP4				40.25 39.75						
5050DP4				50.25 49.75						
5060DP4				60.25 59.75						
5520DP4	55	60	2.505 2.460	20.25 19.75		54.970 54.940		60.030 60.000	55.110 54.990	0.170 0.020
5525DP4				25.25 24.75						
5530DP4				30.25 29.75						
5540DP4				40.25 39.75						
5550DP4				50.25 49.75						
5555DP4				55.25 54.75						
5560DP4				60.25 59.75						
6020DP4	60	65		20.25 19.75		59.970 59.940		65.030 65.000	60.110 59.990	0.170 0.020
6030DP4				30.25 29.75						
6040DP4				40.25 39.75						
6050DP4				50.25 49.75						
6060DP4				60.25 59.75						
6070DP4				70.25 69.75						

All dimensions in mm

8 Standard Products

PART NO.	NOMINAL DIAMETER D_i	NOMINAL DIAMETER D_o	WALL THICKNESS S_3 max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
6530DP4	65	70	2.505 2.460	30.25 29.75	f7	64.970 64.940	H7	70.030 70.000	65.110 64.990	0.170 0.020
6550DP4				50.25 49.75						
6570DP4				70.25 69.75						
7040DP4	70	75		40.25 39.75		69.970 69.940		75.030 75.000	70.110 69.990	
7050DP4				50.25 49.75						
7070DP4				70.25 69.75						
7560DP4	75	80		60.25 59.75		74.970 74.940		80.030 80.000	75.110 74.990	
7580DP4				80.25 79.75						
8040DP4	80	85	2.490 2.440	40.50 39.50	h8	80.000 79.946		85.035 85.000	80.155 80.020	0.209 0.020
8060DP4				60.50 59.50						
8080DP4				80.50 79.50						
80100DP4				100.50 99.50						
8530DP4	85	90		30.50 29.50		85.000 84.946		90.035 90.000	85.155 85.020	
8560DP4				60.50 59.50						
85100DP4				100.50 99.50						
9060DP4	90	95		60.50 59.50		90.000 89.946		95.035 95.000	90.155 90.020	
90100DP4				100.50 99.50						
9560DP4	95	100		60.50 59.50		95.000 94.946		100.035 100.000	95.155 95.020	
95100DP4				100.50 99.50						
10050DP4	100	105		50.50 49.50		100.000 99.946		105.035 105.000	100.155 100.020	
10060DP4				60.50 59.50						
100115DP4				115.50 114.50						
10560DP4	105	110		60.50 59.50		105.000 104.946		110.035 110.000	105.155 105.020	
105115DP4				115.50 114.50						
11060DP4	110	115		60.50 59.50		110.000 109.946		115.035 115.000	110.155 110.020	
110115DP4				115.50 114.50						
11550DP4	115	120		50.50 49.50		115.000 114.946		120.035 120.000	115.155 115.020	
11570DP4				70.50 69.50						
12050DP4	120	125	2.465 2.415	50.50 49.50		120.000 119.946		125.040 125.000	120.210 120.070	0.264 0.070
12060DP4				60.50 59.50						
120100DP4				100.50 99.50						
125100DP4	125	130		100.50 99.50		125.000 124.937		130.040 130.000	125.210 125.070	0.273 0.070
13060DP4	130	135		60.50 59.50		130.000 129.937		135.040 135.000	130.210 130.070	
130100DP4				100.50 99.50						

All dimensions in mm

PART NO.	NOMINAL DIAMETER D_i	D_o	WALL THICKNESS S_3 max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
13560DP4	135	140	2.465 2.415	60.50 59.50	h8	135.000 134.937	H7	140.040 140.000	135.210 135.070	0.273 0.070
13580DP4				80.50 79.50						
14060DP4	140	145		60.50 59.50		140.000 139.937		145.040 145.000	140.210 140.070	
140100DP4				100.50 99.50						
15060DP4	150	155		60.50 59.50		150.000 149.937		155.040 155.000	150.210 150.070	
15080DP4				80.50 79.50						
150100DP4				100.50 99.50						
16080DP4	160	165		80.50 79.50		160.000 159.937		165.040 165.000	160.210 160.070	
160100DP4				100.50 99.50						
180100DP4	180	185		100.50 99.50		180.000 179.937		185.046 185.000	180.216 180.070	0.279 0.070
200100DP4	200	205				200.000 199.928		205.046 205.000	200.216 200.070	0.288 0.070
210100DP4	210	215				210.000 209.928		215.046 215.000	210.216 210.070	
220100DP4	220	225				220.000 219.928		225.046 225.000	220.216 220.070	
250100DP4	250	255				250.000 249.928		255.052 255.000	250.222 250.070	0.294 0.070
300100DP4	300	305				300.000 299.919		305.052 305.000	300.222 300.070	0.303 0.070

All dimensions in mm

8 Standard Products

8.2 DP4® CYLINDRICAL BUSHES - inch sizes



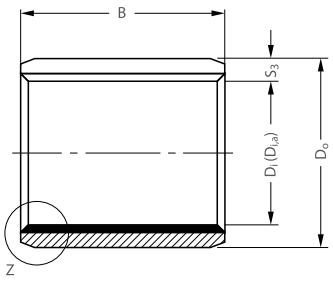

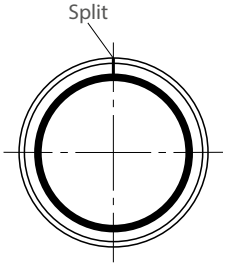

Dimensions and Tolerances according to ISO 3547 and GGB Specifications

PART NO.	TECHNICAL DATA			
	Dimensions			Installation
	Inside Ø D_i	Outside Ø D_o	Width B	$D_{i,a}$
02DP402	1/8	3/16	1/8	0.1268/0.1243
02DP403			3/16	
025DP4025	5/32	7/32	5/32	0.1581/0.1556
025DP404			1/4	
03DP403	3/16	1/4	3/16	0.1893/0.1867
03DP404			1/4	
03DP406			3/8	
04DP404	1/4	5/16	1/4	0.2518/0.2492
04DP406			3/8	
05DP406	5/16	3/8	3/8	0.3143/0.3117
05DP408			1/2	
06DP403	3/8	15/32	3/16	0.3769/0.3742
06DP404			1/4	
06DP406			3/8	
06DP408			1/2	
06DP410			5/8	
06DP412			3/4	
07DP408	7/16	17/32	1/2	0.4394/0.4367
07DP412			3/4	
08DP404	1/2	19/32	1/4	0.5019/0.4992
08DP406			3/8	
08DP408			1/2	
08DP410			5/8	
08DP412			3/4	
08DP414			7/8	
09DP406	9/16	21/32	3/8	0.5644/0.5617
09DP408			1/2	
09DP410			5/8	
09DP412			3/4	
10DP404	5/8	23/32	1/4	0.627/0.6242
10DP408			1/2	
10DP410			5/8	
10DP412			3/4	
10DP414			7/8	
10DP416			1	
11DP414	11/16	25/32	7/8	0.6895/0.6867
12DP404	3/4	7/8	1/4	0.7525/0.7493
12DP406			3/8	
12DP408			1/2	
12DP410			5/8	
12DP412			3/4	
12DP416			1	
14DP404	7/8	1	1/4	0.8775/0.8743
14DP406			3/8	
14DP412			3/4	
14DP414			7/8	
14DP416			1	
14DP420			1 1/4	

All dimensions in inch

PART NO.	TECHNICAL DATA			
	Dimensions			Installation
	Inside Ø D_i	Outside Ø D_o	Width B	$D_{i,a}$
16DP406	1	1 1/8	3/8	1.0026/0.9992
16DP408			1/2	
16DP412			3/4	
16DP416			1	
16DP420			1 1/4	
16DP424			1 1/2	
18DP406	1 1/8	1 9/32	3/8	1.1278/1.124
18DP410			5/8	
18DP412			3/4	
18DP416			1	
20DP406	1 1/4	1 13/32	3/8	1.2528/1.249
20DP412			3/4	
20DP414			7/8	
20DP416			1	
20DP420			1 1/4	
20DP428			1 3/4	
22DP412	1 3/8	1 17/32	3/4	1.3778/1.374
22DP416			1	
22DP424			1 1/2	
22DP428			1 3/4	
24DP408	1 1/2	1 21/32	1/2	1.5028/1.499
24DP416			1	
24DP418			1 1/8	
24DP420			1 1/4	
24DP424			1 1/2	
24DP432			2	
26DP416	1 5/8	1 25/32	1	1.6278/1.624
26DP424			1 1/2	
28DP416	1 3/4	1 15/16	1	1.7535/1.7489
28DP424			1 1/2	
28DP428			1 3/4	
28DP432			2	
30DP412	1 7/8	2 1/16	3/4	1.8787/1.8739
30DP416			1	
30DP430			1 7/8	
30DP436			2 1/4	
32DP408	2	2 3/16	1/2	2.0037/1.9989
32DP416			1	
32DP424			1 1/2	
32DP428			1 3/4	
32DP432			2	
32DP440			2 1/2	
34DP408	2 1/8	2 5/16	1/2	2.1326/2.1262
34DP412			3/4	
34DP416			1	
34DP424			1 1/2	
34DP428			1 3/4	
34DP432			2	
34DP448			3	
34DP464			4	

PART NO.	TECHNICAL DATA			
	Dimensions			Installation
	Inside Ø D_i	Outside Ø D_o	Width B	$D_{i,a}$
40DP416	2 1/2	2 11/16	1	2.5077/2.5013
40DP426			1 5/8	
40DP432			2	
40DP440			2 1/2	
40DP448			3	
40DP456			3 1/2	
40DP460			3 3/4	
40DP464			4	
40DP472			4 1/2	
40DP476			4 3/4	
44DP432	2 3/4	2 15/16	2	2.7566/2.7502
44DP436			2 1/4	
44DP440			2 1/2	
44DP448			3	
44DP456			3 1/2	
44DP460			3 3/4	
44DP464			4	
44DP472			4 1/2	
44DP476			4 3/4	
44DP480			5	
48DP432	3	3 3/16	2	3.0068/3.0002
48DP436			2 1/4	
48DP440			2 1/2	
48DP448			3	
48DP456			3 1/2	
48DP460			3 3/4	
48DP464			4	
48DP472			4 1/2	
48DP476			4 3/4	
48DP480			5	
52DP432	3 1/4	3 7/16	2	3.2568/3.2502
52DP438			2 1/4	
52DP440			2 1/2	
52DP448			3	
52DP456			3 1/2	
52DP460			3 3/4	
52DP464			4	
52DP472			4 1/2	
52DP476			4 3/4	
52DP480			5	
56DP432	3 1/2	3 11/16	2	3.5068/3.5002
56DP438			2 3/8	
56DP440			2 1/2	
56DP448			3	
56DP456			3 1/2	
56DP460			3 3/4	
56DP464			4	
56DP472			4 1/2	
56DP476			4 3/4	
56DP480			5	

PART NO.	TECHNICAL DATA			
	Dimensions			Installation
	Inside Ø D_i	Outside Ø D_o	Width B	$D_{i,a}$
58DP432	3 5/8	3 13/16	2	3.6318/3.6252
58DP436			2 1/4	
58DP440			2 1/2	
58DP448			3	
58DP456			3 1/2	
58DP460			3 3/4	
58DP464			4	
58DP472			4 1/2	
58DP476			4 3/4	
58DP480			5	
60DP432	3 3/4	3 15/16	2	3.7568/3.7502
60DP436			2 1/4	
60DP440			2 1/2	
60DP448			3	
60DP456			3 1/2	
60DP460			3 3/4	
60DP464			4	
60DP472			4 1/2	
60DP476			4 3/4	
60DP480			5	
64DP432	4	4 3/16	2	4.0068/4.0002
64DP436			2 1/4	
64DP440			2 1/2	
64DP448			3	
64DP456			3 1/2	
64DP460			3 3/4	
64DP464			4	
64DP472			4 1/2	
64DP476			4 3/4	
64DP480			5	
68DP432	4 1/4	4 7/16	2	4.2568/4.2502
68DP436			2 1/4	
68DP440			2 1/2	
68DP448			3	
68DP456			3 1/2	
68DP460			3 3/4	
68DP464			4	
68DP472			4 1/2	
68DP476			4 3/4	
68DP480			5	
70DP432	4 3/8	4 9/16	2	4.3818/4.3752
70DP436			2 1/4	
70DP440			2 1/2	
70DP448			3	
70DP456			3 1/2	
70DP460			3 3/4	
70DP464			4	
70DP472			4 1/2	
70DP476			4 3/4	
70DP480			5	
72DP432	4 1/2	4 11/16	2	4.5068/4.5002
72DP436			2 1/4	
72DP440			2 1/2	
72DP448			3	
72DP456			3 1/2	
72DP460			3 3/4	
72DP464			4	
72DP472			4 1/2	
72DP476			4 3/4	
72DP480			5	

PART NO.	TECHNICAL DATA			
	Dimensions			Installation
	Inside Ø D_i	Outside Ø D_o	Width B	$D_{i,a}$
76DP432	4 3/4	4 15/16	2	4.7572/4.7502
76DP436			2 1/4	
76DP440			2 1/2	
76DP448			3	
76DP456			3 1/2	
76DP460			3 3/4	
76DP464			4	
76DP472			4 1/2	
76DP476			4 3/4	
76DP480			5	
80DP432	5	5 3/16	2	5.0056/4.9988
80DP436			2 1/4	
80DP440			2 1/2	
80DP448			3	
80DP456			3 1/2	
80DP460			3 3/4	
80DP464			4	
80DP472			4 1/2	
80DP476			4 3/4	
80DP480			5	
84DP432	5 1/4	5 7/16	2	5.257/5.2502
84DP436			2 1/4	
84DP440			2 1/2	
84DP448			3	
84DP456			3 1/2	
84DP460			3 3/4	
84DP464			4	
84DP472			4 1/2	
84DP476			4 3/4	
84DP480			5	
88DP432	5 1/2	5 11/16	2	5.507/5.5002
88DP436			2 1/4	
88DP440			2 1/2	
88DP448			3	
88DP456			3 1/2	
88DP460			3 3/4	
88DP464			4	
88DP472			4 1/2	
88DP476			4 3/4	
88DP480			5	
92DP432	5 3/4	5 15/16	2	5.757/5.7502
92DP436			2 1/4	
92DP440			2 1/2	
92DP448			3	
92DP456			3 1/2	
92DP460			3 3/4	
92DP464			4	
92DP472			4 1/2	
92DP476			4 3/4	
92DP480			5	
96DP432	6	6 3/16	2	6.007/6.0002
96DP436			2 1/4	
96DP440			2 1/2	
96DP448			3	
96DP456			3 1/2	
96DP460			3 3/4	
96DP464			4	
96DP472			4 1/2	
96DP476			4 3/4	
96DP480			5	

PART NO.	TECHNICAL DATA			
	Dimensions			Installation
	Inside Ø D_i	Outside Ø D_o	Width B	$D_{i,a}$
100DP432	6 1/4	6 7/16	2	6.257/6.2502
100DP436			2 1/4	
100DP440			2 1/2	
100DP448			3	
100DP456			3 1/2	
100DP460			3 3/4	
100DP464			4	
100DP472			4 1/2	
100DP476			4 3/4	
100DP480			5	
104DP432	6 1/2	6 11/16	2	6.507/6.5002
104DP436			2 1/4	
104DP440			2 1/2	
104DP448			3	
104DP456			3 1/2	
104DP460			3 3/4	
104DP464			4	
104DP472			4 1/2	
104DP476			4 3/4	
104DP480			5	
108DP432	6 3/4	6 15/16	2	6.757/6.7502
108DP436			2 1/4	
108DP440			2 1/2	
108DP448			3	
108DP456			3 1/2	
108DP460			3 3/4	
108DP464			4	
108DP472			4 1/2	
108DP476			4 3/4	
108DP480			5	
112DP432	7	7 3/16	2	7.0026/6.9956
112DP436			2 1/4	
112DP440			2 1/2	
112DP448			3	
112DP456			3 1/2	
112DP460			3 3/4	
112DP464			4	
112DP472			4 1/2	
112DP476			4 3/4	
112DP480			5	

All dimensions in inch

8 Standard Products

8.3 DP4® FLANGED BUSHES - metric sizes

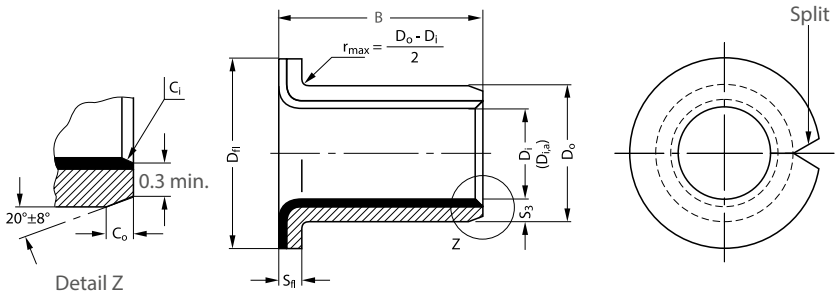

Dimensions and Tolerances according to ISO 3547 and GGB Specifications

OUTSIDE C_o AND INSIDE C_i CHAMFERS

WALL THICKNESS S_3	C_o (a) MACHINED	/ ROLLED	C_i (b)
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5

WALL THICKNESS S_3	C_o (a) MACHINED	/ ROLLED	C_i (b)
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

(a) = chamfer C_o machined or rolled at the option of the manufacturer
(b) = C_i can be a radius or a chamfer in accordance with ISO 13715

PART NO.	NOMINAL DIAMETER D_i	D_o	WALL THICKNESS S_3 max. min.	FLANGE THICKN. S_{fl} max. min.	FLANGE Ø D_{fl} max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
BB0304DP4	3	4.5	0.750 0.730	0.80 0.70	7.50 6.50	4.25 3.75	h6	3.000 2.994	H6	4.508 4.500	3.048 3.000	0.054 0.000
BB0404DP4	4	5.5			9.50 8.50	4.25 3.75		4.000 3.992		5.508 4.500	4.048 4.000	0.056 0.000
BB0505DP4	5	7	1.005 0.980	1.05 0.80	10.50 9.50	5.25 4.75	f7	4.990 4.978	H7	7.015 7.000	5.055 4.990	0.077 0.000
BB0604DP4	6	8			12.50 11.50	4.25 3.75		5.990 5.978		8.015 8.000	6.055 5.990	0.077 0.000
BB0608DP4						8.25 7.75						
BB0806DP4	8	10			15.50 14.50	5.75 5.25		7.987 7.972		10.015 10.000	8.055 7.990	0.083 0.003
BB0808DP4						7.75 7.25						
BB0810DP4						9.75 9.25						
BB1007DP4	10	12			18.50 17.50	7.25 6.75		9.987 9.972		12.018 12.000	10.058 9.990	0.086 0.003
BB1009DP4						9.25 8.75						
BB1012DP4						12.25 11.75						
BB1017DP4						17.25 16.75						
BB1207DP4	12	14			20.50 19.50	7.25 6.75		11.984 11.966		14.018 14.000	12.058 11.990	0.092 0.006
BB1209DP4						9.25 8.75						
BB1212DP4						12.25 11.75						
BB1217DP4						17.25 16.75						
BB1412DP4	14	16			22.50 21.50	12.25 11.75		13.984 13.966		16.018 16.000	14.058 13.990	
BB1417DP4						17.25 16.75						

All dimensions in mm

PART NO.	NOMINAL DIAMETER D_i	NOMINAL DIAMETER D_o	WALL THICKNESS S_3 max. min.	FLANGE THICKN. S_{fl} max. min.	FLANGE Ø D_{fl} max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
BB1509DP4	15	17	1.005 0.980	1.05 0.80	23.50 22.50	9.25 8.75	f7	14.984 14.966	H7	17.018 17.000	15.058 14.990	0.092 0.006
BB1512DP4						12.25 11.75						
BB1517DP4						17.25 16.75						
BB1612DP4	16	18			24.50 23.50	12.25 11.75		15.984 15.966		18.018 18.000	16.058 15.990	
BB1617DP4						17.25 16.75						
BB1812DP4	18	20			26.50 25.50	12.25 11.75		17.984 17.966		20.021 20.000	18.061 17.990	0.095 0.006
BB1817DP4						17.25 16.75						
BB1822DP4						22.25 21.75						
BB2012DP4	20	23	1.505 1.475	1.60 1.30	30.50 29.50	11.75 11.25		19.980 19.959		23.021 23.000	20.071 19.990	0.112 0.010
BB2017DP4						16.75 16.25						
BB2022DP4						21.75 21.25						
BB2512DP4	25	28			35.50 34.50	11.75 11.25		24.980 24.959		28.021 28.000	25.071 24.990	
BB2517DP4						16.75 16.25						
BB2522DP4						21.75 21.25						
BB3016DP4	30	34	2.005 1.970	2.10 1.80	42.50 41.50	16.25 15.75		29.980 29.959		34.025 34.000	30.085 29.990	0.126 0.010
BB3026DP4						26.25 25.75						
BB3516DP4	35	39			47.50 46.50	16.25 15.75		34.975 34.950		39.025 39.000	35.085 34.990	0.135 0.015
BB3526DP4						26.25 25.75						
BB4016DP4	40	44			53.50 52.50	16.25 15.75		39.975 39.950		44.025 44.000	40.085 39.990	
BB4026DP4						26.25 25.75						
BB4516DP4	45	50	2.505 2.460	2.60 2.30	58.50 57.50	16.25 15.75		44.975 44.950		50.025 50.000	45.105 44.990	0.155 0.015
BB4526DP4						26.25 25.75						

All dimensions in mm

8 Standard Products

8.4 DP4® FLANGED BUSHES - inch sizes

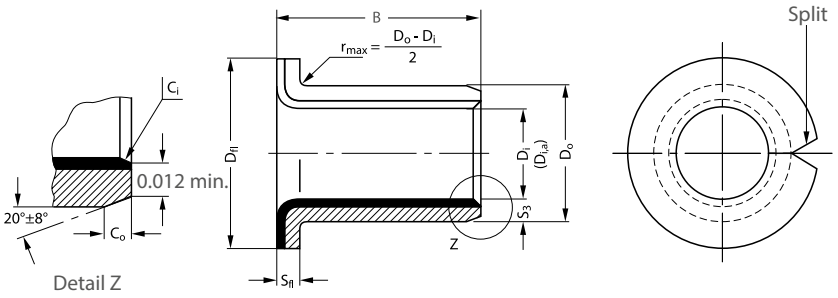

Dimensions and Tolerances according to ISO 3547 and GGB Specifications

PART NO.	TECHNICAL DATA					
	Dimensions					Installation
	Inside Ø D_i	Outside Ø D_o	Width B	Flange Ø D_{fl}	Flange thickness	$D_{i,a}$
06FDP404	3/8	1/2	1/4	2/3	0.047-0.039	0.3779/0.3752
06FDP406			3/8			
06FDP408			1/2			
06FDP412			3/4			
08FDP404	1/2	3/5	1/4	4/5		0.5029/0.5002
08FDP406			3/8			
08FDP408			1/2			
08FDP412			3/4			
10FDP406	5/8	5/7	3/8	1		0.628/0.6252
10FDP408			1/2			
10FDP410			5/8			
10FDP412			3/4			
12FDP406	3/4	7/8	3/8	1 1/4		0.7534/0.7502
12FDP408			1/2			
12FDP412			3/4			
12FDP416			1			
14FDP408	7/8	1	1/2	1 1/4	0.063-0.055	0.8784/0.8752
14FDP412			3/4			
14FDP416			1			
14FDP420			1 1/4			
16FDP408	1	1 1/8	1/2	1 3/8		1.0034/1.0002
16FDP412			3/4			
16FDP416			1			
16FDP420			1 1/4			
20FDP416	1 1/4	1 2/5	1	1 3/4	0.078-0.07	1.254/1.2502
20FDP420			1 1/4			
20FDP424			1 1/2			
24FDP416	1 1/2	1 2/3	1	2		1.504/1.5002
24FDP424			1/2			
24FDP432			2			

All dimensions in inch

8.5 DP4® THRUST WASHERS - metric sizes

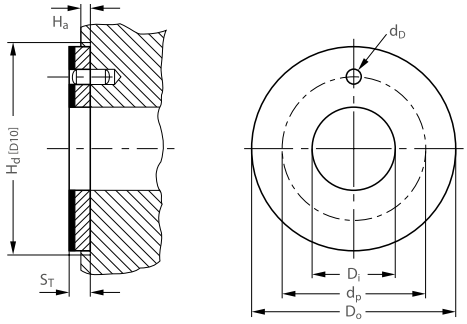

Dimensions and Tolerances according to ISO 3547 and GGB Specifications

PART NO.	INSIDE DIAMETER D_i		OUTSIDE DIAMETER D_o		THICKNESS S_T	DOWEL HOLE Ø d_D	DOWEL HOLE PCD Ø d_p	RECESS DEPTH H_a
	max.	min.	max.	min.	max. min.	max. min.	max. min.	max. min.
WC08DP4	10.25	10.00	20.00	19.75		No Hole	No Hole	
WC10DP4	12.25	12.00	24.00	23.75		1.875 1.625	18.12 17.88	
WC12DP4	14.25	14.00	26.00	25.75			20.12 19.88	
WC14DP4	16.25	16.00	30.00	29.75		2.375 2.125	22.12 21.88	
WC16DP4	18.25	18.00	32.00	31.75			25.12 24.88	
WC18DP4	20.25	20.00	36.00	35.75			28.12 27.88	
WC20DP4	22.25	22.00	38.00	37.75	1.50 1.45		30.12 29.88	1.20 0.95
WC22DP4	24.25	24.00	42.00	41.75		3.375 3.125	33.12 32.88	
WC24DP4	26.25	26.00	44.00	43.75			35.12 34.88	
WC25DP4	28.25	28.00	48.00	47.75			38.12 37.88	
WC30DP4	32.25	32.00	54.00	53.75			43.12 42.88	
WC35DP4	38.25	38.00	62.00	61.75			50.12 49.88	
WC40DP4	42.25	42.00	66.00	65.75		4.375 4.125	54.12 53.88	
WC45DP4	48.25	48.00	74.00	73.75			61.12 60.88	
WC50DP4	52.25	52.00	78.00	77.75	2.00 1.95		65.12 64.88	1.70 1.45
WC60DP4	62.25	62.00	90.00	89.75			76.12 75.88	

All dimensions in mm

8 Standard Products

8.6 DP4® THRUST WASHERS - inch sizes

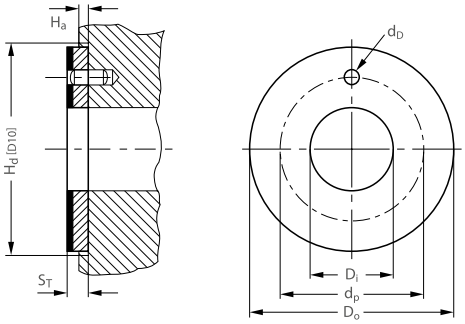

Dimensions and Tolerances according to ISO 3547 and GGB Specifications

PART NO.	TECHNICAL DATA							
	Nominal Dimensions			Installation				
	Inside Ø D_i	Outside Ø D_o	Thickness S_T	Dowel hole Ø	Pitch circle Ø	rd max	rd min	Recess depth
G06DP4	0.5	0.875	0.0605	0.072	0.687	0.05	0.04	0.05-0.04
G07DP4	0.562	1			0.781			
G08DP4	0.625	1.125		0.104	0.875			
G09DP4	0.687	1.187			0.937			
G10DP4	0.75	1.25			1			
G11DP4	0.812	1.375			1.094			
G12DP4	0.875	1.5		0.135	1.187			
G14DP4	1	1.75			1.375			
G16DP4	1.125	2		0.166	1.562			
G18DP4	1.25	2.125			1.687			
G20DP4	1.375	2.25			1.812			
G22DP4	1.5	2.5		0.197	2			
G24DP4	1.625	2.625			2.125			
G26DP4	1.75	2.75			2.25			
G28DP4	2	3	0.0915		2.5	0.08	0.07	0.08-0.07
G30DP4	2.125	3.125			2.625			
G32DP4	2.25	3.25			2.75			

All dimensions in inch. Contact your local Timken representative for additional dimensions.

8.7 DP4® FLANGED WASHERS - metric sizes

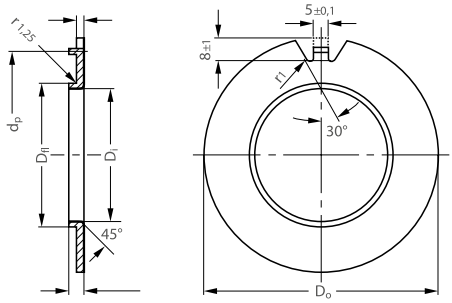

Dimensions and Tolerances according to ISO 3547 and GGB Specifications

PART NO.	INSIDE DIAMETER D_i max. min.	OUTSIDE DIAMETER D_o max. min.	FLANGE Ø D_{fl} max. min.	LOCATION Ø d_P max. min.
BS40DP4	40.7 40.2	75.0 74.5	44.00 43.90	65.0 64.5
BS50DP4	51.5 51.0	85.0 84.5	55.00 54.88	75.0 74.5
BS60DP4	61.5 61.0	95.0 94.5	65.00 64.88	85.0 84.5
BS70DP4	71.5 71.0	110.0 109.5	75.00 74.88	100.0 99.5
BS80DP4	81.5 81.0	120.0 119.5	85.00 84.86	110.0 109.5
BS90DP4	91.5 91.0	130.0 129.5	95.00 94.86	120.0 119.5
BS100DP4	101.5 101.0	140.0 139.5	105.00 104.86	130.0 129.5

All dimensions in mm

8 Standard Products

8.8 DP4® PLATES - metric sizes

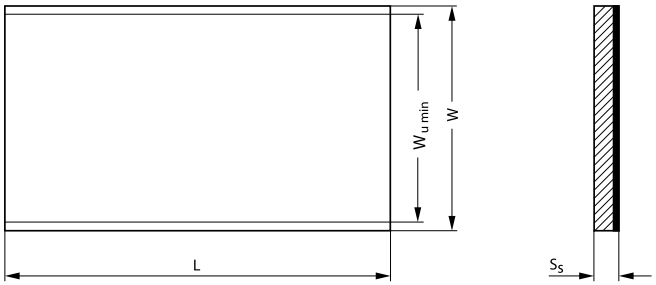

PART NO.	LENGTH L max. min.	TOTAL WIDTH W	USABLE WIDTH $W_{U\ min}$	THICKNESS S_S max. min.
S10190DP4	503 500	200	190	1.01 0.97
S15190DP4				1.52 1.48
S20190DP4				1.98 1.94
S25240DP4		254	240	2.46 2.42

All dimensions in mm

8.9 DP4-B CYLINDRICAL BUSHES - metric sizes



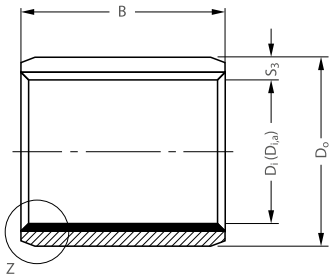

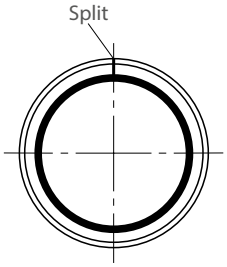

Dimensions and Tolerances according to ISO 3547 and GGB Specifications

OUTSIDE C_o AND INSIDE C_i CHAMFERS

WALL THICKNESS S_3	C_o (a) MACHINED	/ ROLLED	C_i (b)
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5

WALL THICKNESS S_3	C_o (a) MACHINED	/ ROLLED	C_i (b)
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

(a) = chamfer C_o machined or rolled at the option of the manufacturer
(b) = C_i can be a radius or a chamfer in accordance with ISO 13715

PART NO.	NOMINAL DIAMETER D_i	D_o	WALL THICKNESS S_3 max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
0203DP4B	2	3.5	0.750 0.730	3.25 2.75	h6	2.000 1.994	H6	3.508 3.500	2.048 2.000	0.054 0.000
0205DP4B				5.25 4.75						
0306DP4B	3	4.5		6.25 5.75		3.000 2.994		4.508 4.500	3.048 3.000	
0404DP4B	4	5.5		4.25 3.75		4.000 3.992		5.508 5.500	4.048 4.000	0.056 0.000
0406DP4B				6.25 5.75						
0505DP4B	5	7	1.005 0.980	5.25 4.75	f7	4.990 4.978	H7	7.015 7.000	5.055 4.990	0.077 0.000
0510DP4B				10.25 9.75						
0606DP4B	6	8		6.25 5.75		5.990 5.978		8.015 8.000	6.055 5.990	
0608DP4B				8.25 7.75						
0610DP4B				10.25 9.75						
0808DP4B	8	10		8.25 7.75		7.987 7.972		10.015 10.000	8.055 7.990	0.083 0.003
0810DP4B				10.25 9.75						
0812DP4B				12.25 11.75						
1010DP4B	10	12		10.25 9.75		9.987 9.972		12.018 12.000	10.058 9.990	0.086 0.003
1015DP4B				15.25 14.75						
1208DP4B	12	14		8.25 7.75		11.984 11.966		14.018 14.000	12.058 11.990	0.092 0.006
1210DP4B				10.25 9.75						
1212DP4B				12.25 11.75						
1215DP4B				15.25 14.75						

All dimensions in mm

8 Standard Products

PART NO.	NOMINAL DIAMETER D_i	NOMINAL DIAMETER D_o	WALL THICKNESS S_3 max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.	HOUSING Ø D_H [H6, H7] max. min.	BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
1410DP4B	14	16	1.005 0.980	10.25 9.75	13.984 13.966	16.018 16.000	14.058 13.990	0.092 0.006
1415DP4B				15.25 14.75				
1420DP4B				20.25 19.75				
1515DP4B	15	17		15.25 14.75	14.984 14.966	17.018 17.000	15.058 14.990	
1525DP4B				25.25 24.75				
1615DP4B	16	18		15.25 14.75	15.984 15.966	18.018 18.000	16.058 15.990	
1625DP4B				25.25 24.75				
1820DP4B	18	20		20.25 19.75	17.984 17.966	20.021 20.000	18.061 17.990	0.095 0.006
1825DP4B				25.25 24.75				
2015DP4B	20	23	1.505 1.475	15.25 14.75	19.980 19.959	23.021 23.000	20.071 19.990	0.112 0.010
2020DP4B				20.25 19.75				
2025DP4B				25.25 24.75				
2030DP4B				30.25 29.75				
2215DP4B	22	25		15.25 14.75	21.980 21.959	25.021 25.000	22.071 21.990	
2220DP4B				20.25 19.75				
2225DP4B				25.25 24.75				
2515DP4B	25	28		15.25 14.75	24.980 24.959	28.021 28.000	25.071 24.990	
2525DP4B				25.25 24.75				
2830DP4B	28	32	2.005 1.970	30.25 29.75	27.980 27.959	32.025 32.000	28.085 27.990	0.126 0.010
3020DP4B	30	34		20.25 19.75	29.980 29.959	34.025 34.000	30.085 29.990	
3030DP4B				30.25 29.75				
3040DP4B				40.25 39.75				
3520DP4B	35	39		20.25 19.75	34.975 34.950	39.025 39.000	35.085 34.990	0.135 0.015
3530DP4B				30.25 29.75				
4030DP4B	40	44		30.25 29.75	39.975 39.950	44.025 44.000	40.085 39.990	
4050DP4B				50.25 49.75				
4530DP4B	45	50	2.505 2.460	30.25 29.75	44.975 44.950	50.025 50.000	45.105 44.990	0.155 0.015
4550DP4B				50.25 49.75				
5040DP4B	50	55		40.25 39.75	49.975 49.950	55.030 55.000	50.110 49.990	0.160 0.015
5060DP4B				60.25 59.75				
5540DP4B	55	60		40.25 39.75	54.970 54.940	60.030 60.000	55.110 54.990	
6040DP4B	60	65		40.25 39.75	59.970 59.940	65.030 65.000	60.110 59.990	0.170 0.020
6050DP4B				50.25 49.75				
6060DP4B				60.25 59.75				
6070DP4B				70.25 69.75				

All dimensions in mm

PART NO.	NOMINAL DIAMETER D_i	D_o	WALL THICKNESS S_3 max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
6570DP4B	65	70	2.505 2.460	70.25 69.75	f7	64.970 64.940	H7	70.030 70.000	65.110 64.990	0.170 0.020
7050DP4B	70	75		50.25 49.75		69.970 69.940		75.030 75.000	70.110 69.990	
7070DP4B				70.25 69.75						
7580DP4B	75	80		80.25 79.75		74.970 74.940		80.030 80.000	75.110 74.990	
8060DP4B	80	85	2.490 2.440	60.50 59.50	h8	80.000 79.946		85.035 85.000	80.155 80.020	0.201 0.020
80100DP4B				100.50 99.50						
85100DP4B	85	90		100.50 99.50		85.000 84.946		90.035 90.000	85.155 85.020	0.209 0.020
9060DP4B	90	95		60.50 59.50		90.000 89.946		95.035 95.000	90.155 90.020	
90100DP4B				100.50 99.50						
95100DP4B	95	100		100.50 99.50		95.000 94.946		100.035 100.000	95.155 95.020	
10060DP4B	100	105		60.50 59.50		100.000 99.946		105.035 105.000	100.155 100.020	
100115DP4B				115.50 114.50						
105115DP4B	105	110		115.50 114.50		105.000 104.946		110.035 110.000	105.155 105.020	
110115DP4B	110	115		115.50 114.50		110.000 109.946		115.035 115.000	115.155 115.020	

All dimensions in mm

8 Standard Products

8.10 DP4-B FLANGED BUSHES - metric sizes

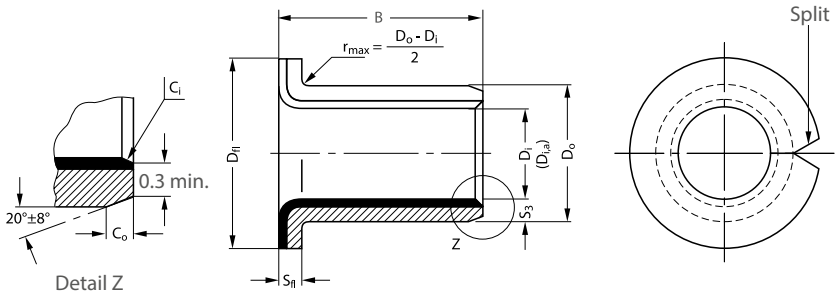

Dimensions and Tolerances according to ISO 3547 and GGB Specifications

OUTSIDE C_o AND INSIDE C_i CHAMFERS

WALL THICKNESS S_3	C_o (a) MACHINED	/ ROLLED	C_i (b)
0.75	0.5 ± 0.3	0.5 ± 0.3	-0.1 to -0.4
1.5	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.7
1	0.6 ± 0.4	0.6 ± 0.4	-0.1 to -0.5

WALL THICKNESS S_3	C_o (a) MACHINED	/ ROLLED	C_i (b)
2	1.2 ± 0.4	1.0 ± 0.4	-0.1 to -0.7
2.5	1.8 ± 0.6	1.2 ± 0.4	-0.2 to -1.0

(a) = chamfer C_o machined or rolled at the option of the manufacturer
(b) = C_i can be a radius or a chamfer in accordance with ISO 13715

PART NO.	NOMINAL DIAMETER D_i	D_o	WALL THICKNESS S_3 max. min.	FLANGE THICKN. S_{fl} max. min.	FLANGE Ø D_{fl} max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
BB0304DP4B	3	4.5	0.750 0.730	0.80 0.70	7.50 6.50	4.25 3.75	h6	3.000 2.994	H6	4.508 4.500	3.048 3.000	0.054 0.000
BB0404DP4B	4	5.5			9.50 8.50	4.25 3.75		4.000 3.992		5.508 4.500	4.048 4.000	0.056 0.000
BB0505DP4B	5	7	1.005 0.980	1.05 0.80	10.50 9.50	5.25 4.75	f7	4.990 4.978	H7	7.015 7.000	5.055 4.990	0.077 0.000
BB0604DP4B	6	8			12.50 11.50	4.25 3.75		5.990 5.978		8.015 8.000	6.055 5.990	0.077 0.000
BB0608DP4B						8.25 7.75						
BB0806DP4B	8	10			15.50 14.50	5.75 5.25		7.987 7.972		10.015 10.000	8.055 7.990	0.083 0.003
BB0810DP4B						9.75 9.25						
BB1007DP4B	10	12			18.50 17.50	7.25 6.75		9.987 9.972		12.018 12.000	10.058 9.990	0.086 0.003
BB1012DP4B						12.25 11.75						
BB1207DP4B	12	14			20.50 19.50	7.25 6.75		11.984 11.966		14.018 14.000	12.058 11.990	0.092 0.006
BB1209DP4B						9.25 8.75						
BB1212DP4B						12.25 11.75						
BB1417DP4B	14	16			22.50 21.50	17.25 16.75		13.984 13.966		16.018 16.000	14.058 13.990	
BB1512DP4B	15	17			23.50 22.50	12.25 11.75		14.984 14.966		17.018 17.000	15.058 14.990	
BB1517DP4B						17.25 16.75						
BB1612DP4B	16	18			24.50 23.50	12.25 11.75		15.984 15.966		18.018 18.000	16.058 15.990	
BB1617DP4B						17.25 16.75						

All dimensions in mm

PART NO.	NOMINAL DIAMETER D_i	D_o	WALL THICKNESS S_3 max. min.	FLANGE THICKN. S_{fl} max. min.	FLANGE Ø D_{fl} max. min.	WIDTH B max. min.	SHAFT Ø D_J [H6, F7, H8] max. min.		HOUSING Ø D_H [H6, H7] max. min.		BUSH Ø $D_{i,a}$ ASSEMBLY IN H6/H7 HOUSING max. min.	CLEARANCE C_D max. min.
BB1812DP4B	18	20	1.005 0.980	1.05 0.80	26.50 25.50	12.25 11.75	f7	17.984 17.966	H7	20.021 20.000	18.061 17.990	0.095
BB1822DP4B						22.25 21.75						0.006
BB2012DP4B	20	22	1.505 1.475	1.60 1.30	30.50 29.50	11.75 11.25		19.980 19.959		23.021 23.000	20.071 19.990	0.112 0.010
BB2017DP4B						16.75 16.25						
BB2512DP4B	25	28			35.50 34.50	11.75 11.25		24.980 24.959		28.021 28.000	25.071 24.990	
BB2522DP4B						21.75 21.25						
BB3016DP4B	30	34	2.005 1.970	2.10 1.80	42.50 41.50	16.25 15.75		29.980 29.959		34.025 34.000	30.085 29.990	0.126
BB3026DP4B						26.25 25.75						0.010
BB3526DP4B	35	39			47.50 46.50	26.25 25.75		34.975 34.950		39.025 39.000	35.085 34.990	0.135 0.015
BB4026DP4B	40	44			53.50 52.50	26.25 25.75		39.975 39.950		44.025 44.000	40.085 39.990	0.135 0.015
BB4526DP4B	45	50	2.505 2.460	2.60 2.30	58.50 57.50	26.25 25.75		44.975 44.950		50.025 50.000	45.105 44.990	0.155 0.015

All dimensions in mm

8.11 DP4-B PLATES - metric sizes

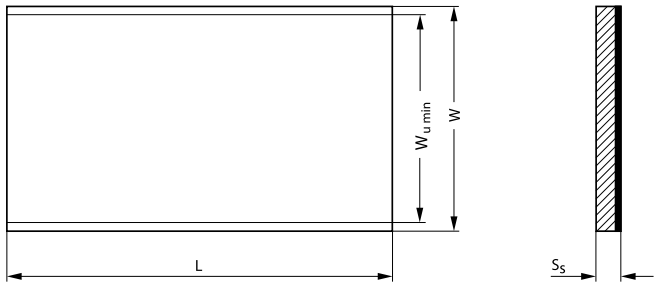

PART NO.	LENGTH L max. min.	TOTAL WIDTH W	USABLE WIDTH $W_{U\,min}$	THICKNESS S_S max. min.
S07085DP4B	503 500	95	85	0.74 0.70
S10180DP4B		195	180	0.74 0.70
S15180DP4B				1.52 1.48
S20180DP4B				1.98 1.94
S25180DP4B				2.46 2.42

All dimensions in mm

9 Test Methods

9.1 MEASUREMENT OF WRAPPED BUSHES

It is not possible to accurately measure the external and internal diameters of a wrapped bush in the free condition. In its free state a wrapped bush will not be perfectly cylindrical and the butt joint may be open. When correctly installed in a housing the butt joint will be tightly closed and the bush will conform to the housing. For this reason the external diameter and internal diameter of a wrapped bush can only be checked with special gauges and test equipment.

The checking methods are defined in ISO 3547 Parts 1 to 7.

TEST A OF ISO 3547 PART 2

Checking the external diameter in a test machine with checking blocks and adjusting mandrel.

TEST A OF ISO 3547 PART 2 ON 2015DP4®	
Checking block and setting mandrel $d_{ch,1}$	23.062 mm
Test force F_{ch}	4500 N
Limits for Δz	0 and -0.065 mm
Bush Outside diameter D_o	23.035 to 23.075 mm

Table 18 : Test A of ISO 3547 Part 2

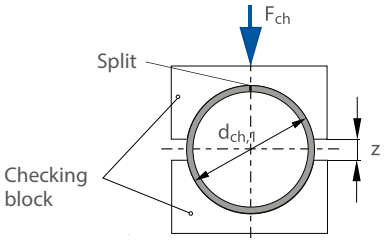

Fig. 40: Test A, data for drawing

TEST B (ALTERNATIVELY TO TEST A)

Check external diameter with GO and NO GO ring gauges.

TEST C

Checking the internal diameter of a bush pressed into a ring gauge, which nominal diameter corresponds to the dimension specified in table 6 of ISO 3547 Part 2 (Example D_i = 20 mm).

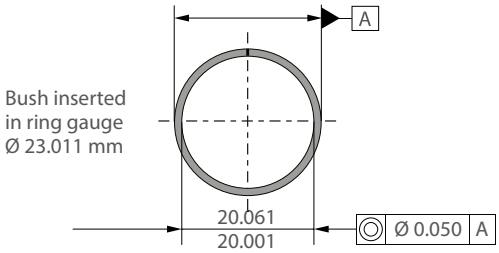

Fig. 41: Test C, data for drawing

MEASUREMENT OF WALL THICKNESS (ALTERNATIVELY TO TEST C)

The wall thickness is measured at one, two or three positions axially according to the bearing dimensions.

B [mm]	X [MM]	MEASUREMENT POSITION
≤15	B/2	1
>15 ≤50	4	2
>50 ≤90	6 and B/2	3
>90	8 and B/2	3

Table 19 : Measurement position

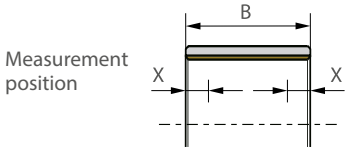

Fig. 42: Test C, measurement position

TEST D

Check external diameter by precision measuring tape.

10 Bearing Application Data Sheet

Please complete the form below and share it with your sales engineer.

DATA FOR BEARING DESIGN CALCULATION

Application: _____

_____

Project/No.: _____ Quantity: _____ ☐ New Design ☐ Existing Design

☐ Steady Load ☐ Rotating Load ☐ Rotational Movement ☐ Oscillating Movement ☐ Linear Movement

DIMENSIONS [MM]

Inside diameter	D_i	
Outside diameter	D_o	
Length	B	
Flange diameter	D_{fl}	
Flange thickness	B_{fl}	
Wall thickness	S_T	
Length of slideplate	L	
Width of slideplate	W	
Thickness of slideplate	S_S	

LOAD

☐ Static load		
☐ Dynamic load		
Axial load F	[N]	
Radial load F	[N]	

MOVEMENT

Rotational speed	N [1/min]	
Speed	V [m/s]	
Length of stroke	L_S [mm]	
Frequence of stroke	[1/min]	
Oscillating cycle 	ϕ[°]	
Osc. frequence	N_{osz} [1/min]	

MATING SURFACE

Material		
Hardness	HB/HRC	
Surface finish	R_a [µm]	

FITS & TOLERANCES

Shaft	D_J	
Bearing housing	D_H	

OPERATING ENVIRONMENT

Ambient temperature T_{amb} [°]	
Bearing housing material	

☐ Housing with good heating transfer properties
☐ Light pressing or insulated housing with poor heat transfer properties
☐ Non metal housing with poor heat transfer properties
☐ Alternate operation in water and dry

OPERATING ENVIRONMENT

☐ Dry
☐ Continuous lubrication
☐ Process fluid lubrication
☐ Initial lubrication only
☐ Hydrodynamic conditions

Process fluid	
Lubricant	
Dynamic viscosity η[mPas]	

SERVICE HOURS PER DAY

Continuous operation	
Intermittent operation	
Operating time	
Days per year	

SERVICE LIFE

Required service life	L_H [h]	

BEARING TYPE

☐ Cylindrical bush



☐ Flanged bush

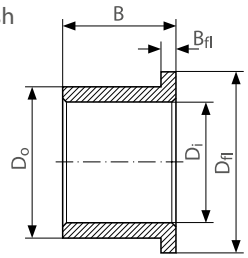

☐ Thrust washer



☐ Slide plate



☐ Special parts (sketch)

CUSTOMER INFORMATION

Company _____

Street _____

City / State / Province / Post Code _____

Telephone _____ Fax _____

Name _____

Email Address _____ Date _____

Formula Symbols and Designations

SYMBOL	UNIT	DESIGNATION
A	mm^2	Surface area of DU® bearing
A_M	mm^2	Surface area of mating surface in contact with DU® bearing (slideway)
a_B	-	Bearing size factor
a_C	-	Application factor for bore burnishing or machining
a_E	-	High load factor
a_{E1}	-	Specific load factor (slideways)
a_{E2}	-	Speed, temperature and material factor (slideways)
a_{E3}	-	Relative contact area factor (slideways)
a_L	-	Life correction constant
a_M	-	Mating surface material factor
a_T	-	Temperature application factor
B	mm	Nominal bush length
C	1/min	Dynamic load frequency
C_D	mm	Installed diametrical clearance
C_i	mm	ID chamfer length
C_o	mm	OD chamfer length
C_T	-	Total number of dynamic load cycles
D_C	mm	Diameter of burnishing tool
D_{fl}	mm	Nominal bush flange OD
D_H	mm	Housing Diameter
D_i	mm	Nominal bush and thrust washer ID
$D_{i,a}$	mm	Bush ID when assembled in housing
D_J	mm	Shaft diameter
D_{Nth}	nvt	Max. thermal neutron dose
D_o	mm	Nominal bush and thrust washer OD
D_Y	Gy	Max. Gamma radiation dose
d_D	mm	Dowel hole diameter
d_L	mm	Oil hole diameter
d_p	mm	Pitch circle diameter for dowel hole
F	N	Bearing load
F_{ch}	N	Test force
F_i	N	Insertion force
f	-	Coefficient of friction

SYMBOL	UNIT	DESIGNATION
H_a	mm	Depth of housing recess (e.g. for thrust washers)
H_d	mm	Diameter of housing recess (e.g. for thrust washers)
L	mm	Strip length
L_H	h	Bearing service life
L_S	mm	Length of stroke (slideway)
N	1/min	Oscillating movement frequency
N_{osz}	1/min	Specific load
P	MPa	Specific load limit
P_{lim}	MPa	Maximum static load
$P_{sta,max}$	MPa	Maximum dynamic load
$P_{dyn,max}$	MPa	Permissible number of cycles
Q	-	Rotational speed
R_a	µm	Surface roughness (DIN 4768, ISO/DIN 4287/1)
R_{OB}	Ω	Electrical resistance
S_3	mm	Bush wall thickness
S_{fl}	mm	Flange thickness
S_S	mm	Strip thickness
S_T	mm	Thrust washer thickness
T	°C	Temperature
T_{amb}	°C	Ambient temperature
T_{max}	°C	Maximum temperature
T_{min}	°C	Minimum temperature
V	m/s	Sliding speed
W	mm	Strip width
$W_{U\ min}$	mm	Minimum usable strip width
Z_T	-	Total number of cycles
α_1	$1/10^6K$	Coefficient of linear thermal expansion parallel to surface
α_2	$1/10^6K$	Coefficient of linear thermal expansion normal to surface
σ_c	MPa	Compressive yield strength
λ	W/mK	Thermal conductivity
φ	°	Angular displacement
η	cP	Dynamic viscosity

Product Information

This document is provided to give you the analysis tools or information to assist you in product selection. Product performance is affected by many factors beyond the control of GGB. Therefore, you must validate the suitability and feasibility of all product selections for your applications.

GGB products are sold subject to GGB's Terms of Sale and Delivery, which include our limited warranty and remedy.
You can find these here: **ggbearings.com/en/terms-and-conditions**, or ask your GGB representative for a copy.

Products are subject to continual development. GGB retains the right to make specification amendments or improvements to the technical data without prior announcement.

DOCUMENT INFORMATION

Edition 2026. This edition replaces earlier editions which hereby lose their validity.

Every reasonable effort has been made to ensure the accuracy of the information in this writing, but GGB assumes no liability for errors or omissions or for any other reason.

HEALTH AND SAFETY

GGB is committed to adhering to all U.S., European and international standards and regulations with regard to lead content. We have established internal processes that monitor any changes to existing standards and regulations, and we work collaboratively with customers and distributors to ensure that all requirements are followed. This includes RoHS and REACH guidelines.GGB is committed to operating in an environmentally conscious and safe manner. We follow numerous industry best practices and are committed to meeting or exceeding a variety of internationally recognized standards for emissions control and workplace safety.

Each of our global locations has management systems in place that adhere to IATF 16949, ISO 9001, ISO 14001 and ISO 45001 quality regulations. Our certificates can be found here: **ggbearings.com/en/company/certificates**.

A detailed explanation of our commitment to REACH and RoHS directives can be found at **ggbearings.com/en/company/reach-rohs**.

TRADEMARKS

GGB® , DP4®, DP4-B, DX®, DX®10, DS and HI-EX® re registered trademarks or trademarks, as the case may be, of GGB and its affiliates.
TIMKEN® is a registered trademark of The Timken Company.
Any use of GGB's trademarks without the trademark owner's prior written permission is strictly prohibited.

©2026 GGB. All rights reserved.

Stronger.**Together.**

GGB BY TIMKEN

ggbearings.com

HB104ENG06-26USA

GGB is part of The Timken Company's portfolio of engineered bearings and industrial motion products.